

Original Research

Hybrid Processes Evaluation of Pb(II) Removal from Wastewater Effluents

Bashkim Thaçi¹, Salih Gashi^{2*}, Nexhat Daci², Majlinda Daci-Ajvazi¹

¹University of Prishtina, Department of Chemistry, 10 000 Prishtinë, Republic of Kosova

²Academy of Sciences and Arts of Kosova, 10 000 Prishtinë, Republic of Kosova

Received: 11 September 2020

Accepted: 13 November 2020

Abstract

The hybrid processes potential on Pb(II) removal from wastewater effluents have been investigated. Batch test conditions were carried out to examine the effects of initial metal concentration, adsorbent dose, contact time, temperature and initial solution pH on adsorption of Pb(II) ions from aqueous solution onto wheat bran. The highest adsorption efficiency was observed at solution pH 5, contact time 30 min and temperature 25°C. The adsorption equilibrium data correlate well with both Langmuir and Freundlich isotherms. Thermodynamic studies suggested the spontaneous and exothermic nature of adsorption process. The retentate of power plants wastewater sample pretreated with wheat bran was used as feed for reverse osmosis low-pressure heterogeneous membrane treatment. The high removal efficiency of Pb(II) and co-existed ions from the above wastewater sample was achieved by hybrid processes with high preference for re-use.

Keywords: adsorption, wheat bran, Pb(II), wastewater, hybrid processes

Introduction

Wastewater effluents of metal-plating and metal finishing operations, mining and ore processing operations: metal processing, battery and accumulator manufacturing operations, thermal power generation (coal-fired plants in particular) nuclear power generation etc. discharged into water and soil directly or indirectly without treatment, have become the major pollutants in water resources among others heavy metal ions. Metals such as lead, cadmium, nickel, mercury and chromium even in small concentration are the most dangerous industrial pollutants of water due to their high toxicity and non-degradability. Lead is one of the

most toxic heavy metal found in industrial wastewater. Lead damages circulatory and central nervous system diseases of the kidneys, liver and reproductive system, basic cellular processes and brain functions. Numerous techniques have been developed for the treatment of heavy metal-bearing effluents. The conventional methods available for removal of heavy metal such chemical precipitation, ion exchange, electrochemical treatment, chemical oxidation/reduction, solvent extraction, membrane filtration etc. are costly, produce some toxic sludge and also require large energy input, which is in efficient, and non is able to completely remove Pb(II) ions.

Adsorption is recognized as an effective method for heavy metal wastewater treatment and search has been focused on the use of agricultural by-products as adsorbents for treatment wastewater effluents due to

*e-mail: salihgashi@ashak.org

their selectivity, low cost and ease used. The inherent advantages and applications of biosorption have been extensively reviewed by several researchers [1-3].

Several biosorption materials have been used for lead adsorption from aqueous solutions. Groundnut hull [4], Moringa oleifera tree leave schemically modified [5], (chalf, rice husk, sesame husk, sun flowers husk), [6], peels of banana [7], etc. have been investigated to remove Pb(II) from wastewater. Moreover, Brassica nigra without any chemical pretreatment is shown to be alternative biosorbent for Pb(II) removal from aqueous solutions in form of metal complex [8]. The Peanut shell is regarded as effective economical biosorbent for the removal of toxic heavy metal ions from solution containing sodium chloride and amino acid, such as marine protein hydrolysate solution [9]. The adsorption of Pb²⁺ in aqueous solution onto activated carbon produced from wine making waste showed successful removal of Pb(II) from polluted water [10].

The *Trapa bispinosa*'s peel (pretreated and modified with HNO₃, HClO₄, and H₂O₂) was exploited to enhance the Pb(II) removal [11].

Soya bean was used for adsorptive removal of lead and arsenic from wastewater. The adsorption by it was an exothermic process [12]. A Pb(II) imprinted magnetic biosorbent (Pb(II)-IMB) was developed for the removal of Pb(II) via lead ion imprinted technology and crosslinking reactions among chitosan (CTS), *Serratia marcescens* and Fe₂O₃ [13]. The Pb²⁺biosorption from aqueous solution by live and dead biosorbents of the hydrocarbon-degrading strain *Rhodococcus* sp.HX-2 was examined. It was conducted that, dead biosorbent seem to be a more effective for application in wastewater treatment [14]. The polyphenols extracted from *Leucaena leucocephala* residues was used for simultaneous removal of Pb(II) and Cd(II) ions from water system. They found that chemisorption might be the mechanism of the solute ion-lllep-s interaction [15]. The lemon, artichoke and bean shells were used to remove (Pb) ions from aqueous solution Bean shell was the most effective [16].

The dominance of Pb(II) during competitive biosorption from multi-metal system was reviewed. For most biosorbents Pb(II) is effectively removed from solution even in presence of other heavy metals. However, the removal of Cu(II), Cd(II), Zn(II), Ni(II) and Cr(III) would be significantly suppressed in the presence of Pb(II) [17]. The 95.7% of coomassie brilliant blue (CBB) was shown to be removed from aqueous solution onto wheat bran [18].

The membrane technology has proven to be a more favorable option in wastewater treatment processes in recent time. Pressure driven membrane processes are by so far the most widely applied membrane processes in water treatment from pretreatment to post-treatment of wastewater. Among the pressure driven membrane processes RO is highly known for its efficiency in separating small particles including bacteria and monovalent ions like sodium and

chloride ions up to 99.5% [19]. It is evident that no adsorption nor membrane technologies could be applied individually for successful treatment wastewater of reuse standards. Therefore, the integral part in the success of membrane process is pretreatment, which do not only reduce membrane fouling but also contribute to energy utilization. The possibility of combining two or more membrane processes with each other or other forms of technologies in a hybrid fashions is also continuously being explored, developed and applied in many wastewater treatment facilities. Physicochemical methods such as coagulation/adsorption and softening have been applied in several instances to pretreated wastewater before membrane separation [20]. The purification of olive mill wastewater was studied by combination of Ultrafiltration/Reverse osmosis [21]. Hybrid membrane bio-system for sustainable treatment of oil and gas produced water and fracturing flow back water was investigated [22]. The olive waste, maize cob and wheat bran were used for removal of heavy metal ions from aqueous solutions as well as from wastewater effluents of mining flotation process. It was concluded that these biosorbents could be feasible and sustainable for pretreatment of wastewaters prior to reverse osmosis [23].

This paper aims to evaluate the removal of Pb(II) ions from wastewater effluents by hybrid (biosorption/Reverse osmosis) processes.

Material and Methods

The wheat bran used in this study is a by-product of local flour factory (Dardania, Pejë, Republic of Kosova). It was washed with distilled water and dried (80°C) for 20 hours. The dried samples were saved (0.1 mesh), and fractions of >0.2 mm were used for experiments. The characteristics of used adsorbent are described elsewhere [23]. The sorption of Pb(II) ions on wheat bran was studied using batch technique. The stock solution of reagent grade PbCl₂ of different concentrations Pb(II) (70, 35, 17.5 and 7 mg/dm³) was used in all experimental runs. The 50cm³ of Pb(II) solution was equilibrated with 0.25 g wheat bran at different equilibrated time (5, 10, 20, 30, 60, 90, and 120min). Then 50 cm³ of Pb(II) solution was treated with (0.1, 0.25, and 0.5g of adsorbent), at different temperature (298, 308, 318, 328K), and pH (3, 5, 7, 9, 11) in a stopped Pyrex glass flask in thermostatic shaker bath. After equilibration the suspension was filtered (MN 640m Ø125mm) and retentate was used as feed for reverse osmosis experiments. The thermal power plants (Kosova B) wastewater sample of initial pH 8.35 was treated with wheat bran and filtered with the same filter above. The clear filtrate (retentate) at pH 7.55 without any addition of chemical agents was used in Reverse Osmosis experiment.

The concentration of metals in feed, after adsorption by wheat bran and after reverse osmosis, was

analyzed by inductive coupled plasma optical emission spectroscopy (ICP-OS 21000DV).

The retentate of wheat bran pretreatment was subjected to heterogeneous asymmetric reverse osmosis membranes (batch 317). The reverse osmosis film details and experimental reverse osmosis procedure is described elsewhere [24, 25].

The removal percentage, ($R\%$), and capacity of Pb(II) ions per gram wheat bran at equilibrium, q_e (mg/g) were calculated using the following equations:

$$R\% = \frac{C_o - C_e}{C_o} \times 100 \quad (1)$$

$$q_e = \frac{C_o - C_e}{W} \times V \quad (2)$$

...where C_o and C_e are the initial and equilibrium concentrations of Pb(II) ions, respectively (mg/dm³), V is the volume of Pb(II) solution (dm³), and W is the weight of wheat bran used (g).

Results and Discussion

The adsorption of lead (II) ions into wheat bran was investigated as a function of the contact time, initial metal ion concentration, adsorbent dosage, temperature and initial pH.

The Effect of Initial Sorbate Concentration and Contact Time

The effect of different initial Pb(II) ions concentration on the wheat bran at different contact times are shown in Fig 1.

The rate of Pb(II) binding with the wheat bran is higher in the initial stage, gradually increase, and becoming almost constant. It is evident that contact time of 30 minutes was sufficient to achieve adsorption equilibrium. Therefore, an equilibrium time of 30 minutes was selected for further all studies. The adsorbent dose determines the capacity of an adsorbent for a given initial concentration of the adsorbate. The effect of wheat bran dose and initial concentration on the adsorption of Pb(II) ions is presented in Table 1.

The data of Table 1, indicate that as the initial Pb(II) ion concentration decreases, the percent removal

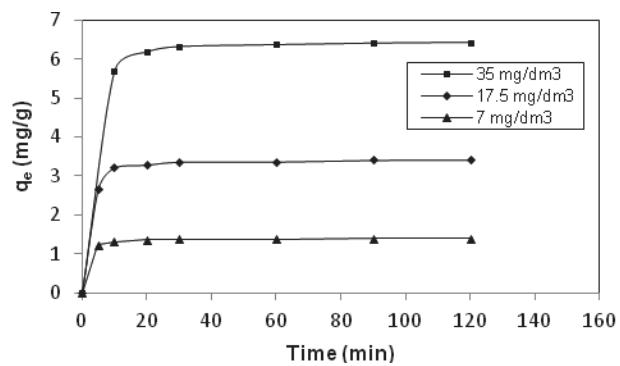


Fig. 1. The rate of adsorption of three initial Pb(II) ion concentrations on the wheat bran vs. contact time. Conditions: wheat bran 0.25 g/50 cm³, 25°C, pH = 5.

increases. The higher removal of metal ions at lower initial concentration is due to the availability of more adsorption binding sites at the initial stage. At lower metal ion concentrations, sufficient adsorption sites are available for the sorption of metal ions. At higher concentrations lower adsorption yield is due to the saturation of adsorption sites of adsorbent.

The adsorption percent at various doses of wheat bran from 0.1-0.5 g is shown in Table 1.

Increasing the adsorbent dose increase the adsorption percent of Pb(II) ions, which is due to the increasing in adsorption sites of adsorbent resulting from increasing of surface area. This was expected as with increasing concentration of adsorbent more active sites become available for metal uptake. This seems to be due to the binding of almost all ions to the adsorbent and the establishment of equilibrium between the ions bound to the adsorbent and those remaining unadsorbed in solution.

The Effect of Initial pH

The pH is a very important parameter in adsorption process. The effect of solution of pH on the adsorption of Pb(II) ions on the wheat bran was investigated from pH 3-11 (Fig 2).

It could be observed that the Pb(II) adsorption by wheat bran increases with increasing pH from 3-8, for all used initial concentrations, becomes rather constant to pH 9, and then decreases rapidly. The lowest value of lead uptake was obtained when pH was minimum

Table 1. Effect of adsorbent dose (g/50 cm³) and initial concentration on adsorption of Pb(II) ions on wheat bran. Conditions: 30 min, pH = 5, 25°C.

| Adsorbent dose (g) | Initial conc. of Pb ²⁺ (mg/dm ³) | | | | Removal efficiency x 10 ² (%) | | | | q _e (mg/g) | | | |
|--------------------|---|----|------|---|--|-------|-------|-------|-----------------------|-------|------|------|
| | | | | | 0.849 | 0.868 | 0.908 | 0.921 | 29.74 | 15.19 | 7.95 | 3.22 |
| 0.1 | | | | | 0.849 | 0.868 | 0.908 | 0.921 | 29.74 | 15.19 | 7.95 | 3.22 |
| 0.25 | 70 | 35 | 17.5 | 7 | 0.893 | 0.903 | 0.962 | 0.986 | 12.49 | 6.32 | 3.37 | 1.38 |
| 0.5 | | | | | 0.959 | 0.966 | 0.973 | 0.991 | 6.72 | 3.38 | 1.70 | 0.69 |

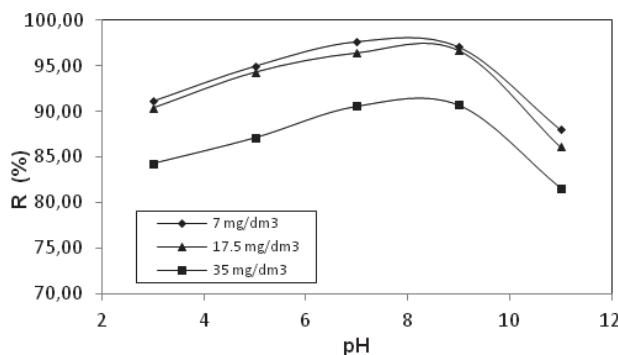


Fig. 2. The effect of pH on removal of Pb (II) on wheat bran, conditions: adsorbent dose 0.25 g/50 cm³, 25°C.

(about 3), as a result of strong acidic medium. This could be due to the excess hydrogen ions surrounding the binding sites making adsorption unfavorable. As the pH increased the overall surface on wheat bran became negative and adsorption increased. Therefore, the Pb(II) ions up to pH 8 would be interact more strongly with negatively charged binding sites. At higher pH>9 the adsorption is followed by precipitation, respectively cations react with hydroxide ions and precipitate as hydroxides.

Adsorption Isotherms Study

Equilibrium study that gives the capacity of the adsorbent and adsorbate are described by adsorption isotherms, which represents the ratio between the quantity adsorbed and that remained in solution at equilibrium at constant temperature.

Several methods are often employed to interpret the equilibrium data. In the present study, the Langmuir and Freundlich adsorption isotherm models were used to explain the experimental results. The Langmuir isotherm describes monolayer adsorption on the surface of an adsorbent with a finite number of identical adsorption sites and no interaction between sites. The model is expressed as follows:

$$\frac{1}{q_e} = \frac{1}{q_{max}} + \frac{1}{K_L q_{max}} \frac{1}{C_e} \quad (3)$$

Linear form of the Equation 3 after rearrangement is given by:

$$\frac{C_e}{q_e} = \frac{1}{K_L q_{max}} + \frac{1}{q_{max}} C_e \quad (4)$$

...where, q_{max} is the monolayer adsorption capacity (the maximum amount adsorbed) of the adsorbent (mg/g). The Langmuir adsorption constant K_L (dm³/mg) is an affinity parameter related to the energy of biosorption, C_e is the equilibrium metal ion concentration in the solution (mg/dm³) and q_e is the equilibrium metal ion concentration on the adsorbent (mg/g). When

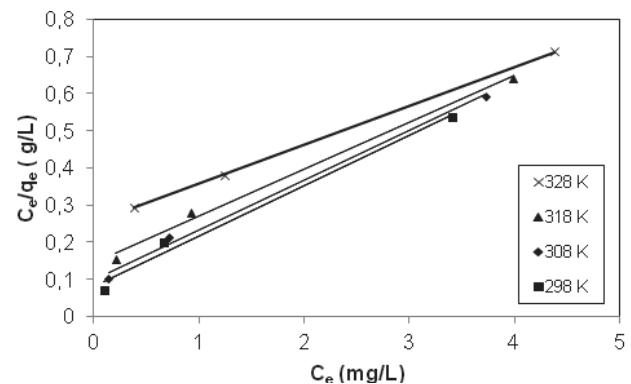


Fig. 3. Langmuir isotherm for Pb(II) ion adsorption at different temperatures, dose of adsorbent 0.25 g/50 cm³.

C_e/q_e is plotted against C_e , the values of q_{max} and K_L were obtained from the slope and the intercept, which shows that adsorption of Pb(II) followed Langmuir isotherm model (Fig. 3).

The essential characteristics of a Langmuir isotherm can be described by a dimensionless constant separation factor or equilibrium parameter, R_L which is defined by Equation 5:

$$R_L = \frac{1}{(1+K_L C_0)} \quad (5)$$

...where C_0 is initial metal concentration (mg/dm³) and K_L is Langmuir constant. The separation factor R_L indicates the isotherm shape as: $R_L < 1$ favorable, $R_L > 1$ unfavorable, $R_L = 1$ linear, $R_L = 0$ irreversible. The data of equilibrium parameter R_L are given in Table 2.

The R_L at different concentrations and temperatures (Table 2) are between 0 and 1, indicating a highly favorable adsorption of Pb(II) ion onto wheat bran.

The Freundlich model isotherm proposes heterogeneous energetic distribution of active sites. The Freundlich isotherm describes reversible adsorption and is not restricted to the formation of a monolayer. The Freundlich model isotherm accompanied by interaction between adsorbed molecules. The Freundlich is an empirical equation (used to estimate the adsorption intensity of the sorbent toward the adsorbate) which is given by:

$$q_e = K_F C_e^{1/n} \quad \log q_e = \log K_F + 1/n \log C_e \quad (6)$$

Table 2. Equilibrium parameters (R_L).

| C_0 (mgL ⁻¹) | 298 K | 308 K | 318 K | 328 K |
|----------------------------|-------|-------|-------|-------|
| 7 | 0.192 | 0.162 | 0.112 | 0.056 |
| 17.5 | 0.087 | 0.071 | 0.048 | 0.023 |
| 35 | 0.043 | 0.037 | 0.024 | 0.012 |

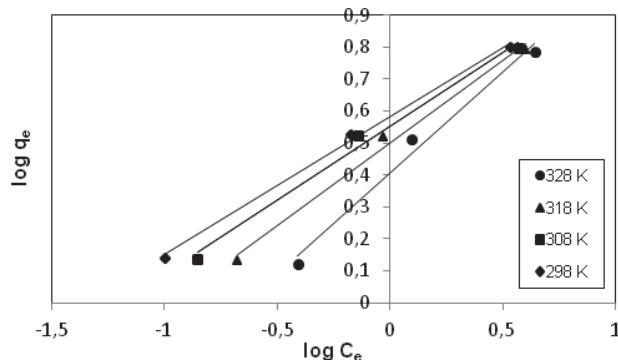


Fig. 4. Freundlich isotherm for adsorption of Pb(II) ion, at different temperatures and adsorption dose 0.25 g/50 cm³.

...where K_F and n are Freundlich constants, K_F (mgg⁻¹) (Lmg⁻¹) is related to uptake (adsorption) capacity and $1/n$ is an empirical parameter related to the adsorption intensity, which varies with the heterogeneity of the material.

The constants K_F and $1/n$ were calculated from the slope and intercept Fig. 4.

Langmuir and Freundlich isotherm data are presented in Table 3.

The data in Table 3, show that the adsorption of Pb(II) ion on what bran fits well with the Langmuir and Freundlich isotherms. The correlation coefficient values (Table 3) approaching to one clearly suggests that Langmuir and Freundlich isotherms holds good to explain adsorption of Pb(II) ions on wheat bran. The R^2 of Langmuir model is slightly higher than Freundlich isotherm.

Confirming that, Pb(II) adsorption occurs on a homogeneous adsorbent surface. Forming a monolayer in which each adsorption site can take a single molecule of adsorbate with the same adsorption energy [26]. Table 3 shows the values of q_{max} decreased as the solution's temperature increased. The decreasing values of q_{max} with increasing temperature indicate that the Pb(II) ions are favorably adsorbed by wheat bran at low temperature, which shows that the adsorption process is exothermic. According to the results the Freundlich model was found to describe also adsorption successfully. The values of K_F was decreased with increase the temperature of solution and $1/n$ increase

with increase of temperature. In addition, $1/n$ was between 0 and 1 indicating that the sorption of Pb(II) ions into wheat bran was favorable under mentioned conditions.

The effect of a change in temperature on the sorption system was studied to determine the thermodynamic parameters of the process.

The effect of temperature of Pb(II) ions was studied by varying the temperature in the range 298-328K. The value of Gibbs free energy ΔG° can be calculated by using the following equation:

$$\Delta G^\circ = -RT \ln k_e, \quad (7)$$

k_e , equilibrium constant is given by following equation:

$$k_e = q_e/C_e \quad (8)$$

k_e is calculated at different temperatures using equation 8.

The relationship between Gibbs free energy change, entropy change (ΔS°) and enthalpy change (ΔH°) can be expressed as:

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (9)$$

From Eqs (7, 9) we obtained:

$$\ln k_e = -\Delta H^\circ/RT + \Delta S^\circ/R$$

...where ΔH° , ΔS° are standard enthalpy and entropy change.

The values of ΔH° and ΔS° were calculated from the slope and the intercept of the linear plot of $\ln k_e$ vs $1/T$ Fig 5.

The thermodynamic parameters of Pb(II) ions adsorption on wheat bran are given in Table 4.

The results (Table 4) show that as temperature of solution increased the equilibrium removal of metal ions was decreased suggesting that temperature has the negative effect on the adsorption of Pb(II) ions onto wheat bran.

The magnitude of ΔG° decreased with decreased temperature indicating spontaneous nature of the adsorption with high preference of metal ion for

Table 3. Langmuir and Freundlich constants of adsorption system at different temperatures.

| Langmuir isotherm parameters | | | | Freundlich isotherm parameters | | |
|------------------------------|--------------------------------|----------------------------|-------|--------------------------------|--|-------|
| T (K) | q_{max} (mgg ⁻¹) | K_L (Lmg ⁻¹) | R^2 | 1/n | K_F (mgg ⁻¹)(Lmg ⁻¹) | R^2 |
| 298 | 12.345 | 0.600 | 0.989 | 0.432 | 3.810 | 0.997 |
| 308 | 10.101 | 0.739 | 0.995 | 0.462 | 3.556 | 0.989 |
| 318 | 6.993 | 1.135 | 0.995 | 0.517 | 3.162 | 0.991 |
| 328 | 3.968 | 2.400 | 0.999 | 0.632 | 2.540 | 0.984 |

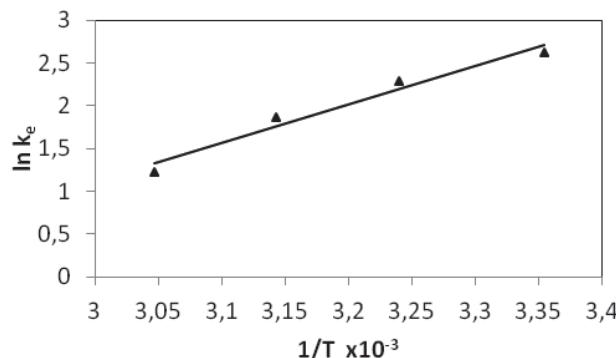


Fig. 5. Plot of $\ln k_e$ vs $1/T$ for Pb(II) ions adsorption by wheat bran at different temperatures, initial conc. 7 mg/dm³ and adsorbent dose 0.25 g/50 cm³.

Table 4. The thermodynamic parameters for adsorption of Pb(II) on wheat bran.

| T (K) | $\ln k_e$ | ΔG° (kJ/mol) | ΔH° (kJ/mol) | ΔS° (kJ/Kmol) |
|-------|-----------|------------------------------|------------------------------|-------------------------------|
| 298 | 2.6246 | -6.50 | -37.52 | -0.104 |
| 308 | 2.2824 | -5.844 | | |
| 318 | 1.8666 | -4.935 | | |
| 328 | 1.2207 | -3.328 | | |

wheat bran, i. e. adsorption was more favorable at low temperature. It was found that Pb(II) adsorption on wheat bran has negative values of the enthalpy change ΔH° which means that adsorption is exothermic process. According to the absolute value of 37.52 kJ/mol the Pb(II) adsorption on wheat bran could be physical-chemical process rather than pure physical or chemical respectively. Negative value of ΔS° suggests a decrease in randomness at the solid/solution interface during the adsorption process and reflects the affinity of the wheat bran for Pb(II) ions, while low value of ΔS° indicates that no remarkable change on entropy occurs.

Although most industrial effluents are composed of a multi-metal system, relatively fewer studies have been conducted on competitive coexisting removal of metal ions from multi-metal systems compared to single-metal solution and also hybrid processes. In the present work the adsorption of Pb(II) ions was near the same in single compared to multi-metal ions in aqueous solution, $q = 5.46$ mg/g or 91%, and $q = 5.44$ mg/g or 90.74% for the relatively near the same metal concentration.

It is evident that adsorption of Pb(II) ion was much higher of other metal ions i.e. wheat bran had strong affinity to Pb(II) ion from aqueous solution that other competitive ions. Therefore, Pb(II) ion is effectively removed from solution in presence of other metal ions. However, the removal of Cd(II) ions for example was lowered significantly $q = 4.24$ mg/g or 67% in comparison with $q = 2.33$ mg/g or 38.33% in presence of Pb(II) ions respectively. The other metal ions were

also suppressed in presence of Pb(II) ion, the results consistent with those published in literature [18].

In the current study the experimental results of the uptake of thermal power plants wastewater system conducted under the same conditions as batch experiments at pH 8.35 are given in Table 5.

The order of metal ions uptake from used wastewater sample was as follows:



This uptake order is understandable due to preference of surface charged groups of wheat bran for specific ions, hydration energy of ions, ionic radius, electronegativity etc.

Although the removal efficiency of Pb(II) ions by wheat bran was lowered compared to single and multi-metal synthetic system in aqueous solution (Table 5), its uptake is comparable with high removal efficiency adsorbents [13].

The data presented in Table 5 shows that removal of Pb(II) and most co-existing ions by wheat bran was very high in thermal power plants wastewater effluents. Thus wheat bran looks preferable biosorbent for waste water treatment containing metal ions of low concentration. It exhibits also significant potential for pre-treatment of such and similar wastewater prior reverse osmosis treatment.

Therefore, the retentate of power plants wastewater sample pretreated with wheat bran as biosorbent was used for reverse osmosis test (Table 5). These results confirm that removal of Pb(II) and coexisting metal ions of pretreated water (retentate) could attain 100% by hybrid processes under experimental conditions used in this work. The resultant effluent seems promising for water re-use.

Table 5. The data of heavy metal content in wastewater effluents sample of thermal power plants (Kosova B), pretreated with wheat bran and treated by heterogeneous reverse osmosis membranes (batch 317) at pressure 1,76 MPa. Specific conductivity: 337 μs at 25°C, COD 13.8 mg/dm³.

| Elements | Feed (mg/dm ³) | Pretreated with wheat bran (mg/dm ³) | Treated with RO (mg/dm ³) |
|----------|-------------------------------|--|---|
| Pb | 0.072 | 0.011 | <1ppb |
| Cd | 0.011 | <1ppb | <1ppb |
| Ni | 0.007 | 0.001 | <0.5ppb |
| Zn | 0.091 | 0.038 | 0.003 |
| Mn | 0.32 | 0.071 | 0.004 |
| Cr | 0.005 | <1ppb | <1ppb |
| pH | 8.35 | 7.55 | 7.70 |

Conclusions

The rapid uptake and high removal efficiency of Pb(II) ions with wheat bran express favorable adsorption of Pb(II) ions from aqueous solutions. The adsorption process was dependent upon the pH of medium, contact time, ion concentration and adsorbent dose. The adsorption equilibrium data fit well both Langmuir and Freundlich adsorption isotherms. The thermodynamic parameters showed the spontaneous and the exothermic nature of the adsorption process. The results of Pb(II) and other coexisting ions removal from wastewater effluents of power plants pre-treated by wheat bran showed good performance for use prior reverse osmosis treatment. Hybrid processes seem to be effective for successful rejection Pb(II) and other metal ions from wastewater justifying their application for water re-use.

Conflict of Interest

The authors declare no conflict of interest.

References

- WANG J., CHEN C. Biosorbents for heavy metals removal and their future. *Biotechn. Adva.* **27** (2), 195, **2009**.
- MATHEW B.B., JAISHANKAR M., BIJU V.G., BEEREGOWDA K.N. Role of Biosorbents in Reducing Toxic Metals. *J. of Toxicol.* **13** (10), 1, **2016**.
- PARK D., YUN J. S. The past, present, and future trends of biosorption. *Biotech. and Biopro. Engin.* **15** (1), 86, **2010**.
- QAISER S., SALEEMI A. R., UMAR M. Biosorption of lead(II) and Cr(VI) on ground nut hull: Equilibrium, kinetics and thermodynamics study. *Elect. J. of Biotech.* **12** (4), 1, **2009**.
- REDDY D.H.K., HARINARTH Y., SESHAIAH K., REDDY A.V.R. Biosorption of Pb(II) from aqueous solutions using chemically modified *Moringa oleifera* tree leaves. *Chem. Engin. J.* **162** (2), 626, **2010**.
- KAFIA M., SURCHI SH. Agricultural Wastes as Low Cost Adsorbents for Pb Removal: Kinetics, Equilibrium and Thermodynamics, *Intern. J. of Chem.* **3** (3), 103, **2011**.
- ANWAR J., SHAFIQUE U., ZAMAN W., SALAM M., DAR A., ANWAR Sh. Removal of Pb (II) and Cd (II) from water by adsorption on peels of banana. *Biosur. Technol.* **101** (6), 1752, **2010**.
- ATA S., DIN M.I., RASOL A., QASIM I., MOHSIN I. U., Equilibrium, Thermodynamics and Kinetic Sorption Studies for the Removal of Coomaassie Brilliant Blue on Wheat Bran as a low-Cost Adsorbent. *J. of Anal. Meth. Chem.* **20** (3), 8, **2012**.
- WARREN R-R., WALTER J.C-V., MARIA E.K-S., WALTER F.Z.A., RICARDO A.Y.P., Evaluation of Pb (II) Adsorption from Aqueous Solutions Using *Brassica nigra* as a Biosorbent. *The Open Biotech. J.* **13**, (1), 77, **2019**.
- XIOA-KUN Y.O., LE-PING Y., ZHENG-SHUM W. Adsorption of Pb²⁺ from solution using Peanut Shell as Biosorbent in the Presence of Amino Acid and Sodium Chloride, *BioResources*. **9** (2), 2446, **2014**.
- FRANCISCA J A., LORENA A., IRENE G-D., FELIX A L, Removal of Pb²⁺ in Wastewater via Adsorption onto an Activated Carbon Produced from Winemaking Waste. *Metals*. **697** (8), 1, **2018**.
- MUHAMMAD N.Z., MUYNNA S., RAZIYA N., SAJJAD H.S., SYED S.SH., MUHAMMAD AQ. Chemical pretreatments of *Trapabispinosa*'s peel (TBP) biosorbent to enhance adsorption capacity for Pb(II). *Open Chem.* **17** (1), 325, **2019**.
- NISHA G., AAYUSH K., MAHAVIR Y., ARCHANA T., Adsorptive removal of lead and arsenic from aqueous solution using soya bean as a novel biosorbent: equilibrium isotherm and thermal stability studies, *Appl. Water Scien.* **8** (4), 98, **2018**.
- YAYUAN H., PIAN W., WEN X., GUIYIN L., JIECAN Y., YAFEI H., CUIMEI CH., PING D., YANYING D., Efficient removal of Pb(II) from aqueous solution by a novel ion imprinted magnetic biosorbent: Adsorption kinetics and mechanisms. *PLoS ONE*. **14** (3), 1, **2019**.
- XIN H., JIACHANG C., HANYU Y., DAHUI L., YUE Q., JIALIN Z.H., ZHIXIA Z.H., LEI H. Pb²⁺ biosorption from aqueous solutions by live and dead biosorbents of the hydrocarbon-degrading strain *Rhodococcus* sp. HX-2. *PLoS ONE*. **15** (1), 24, **2020**.
- CIMA-MUKUL C.A., YOUNESS A., MOHAMED A., JOEL V., ARLETTE A.S., JESUS A.B.Z. Eco-Efficient Biosorbent Based on *Leucaena leucocephala* Residues for the Simultaneous Removal of Pb(II) and Cd(II) Ions from Water System: Sorption and Mechanism. *Bioinorg. Chem. and Applic.* **13** (1) 1, **2019**.
- FEYZA E., SERIF T., VEDIA N.T. Removal of lead from aqueous solutions by low cost and waste biosorbents (lemon, bean and artichoke shells). *Water Sci. and Tech.* **81** (1), 159, **2020**.
- COURTIE M. On the dominance of Pb during competitive biosorption from multi-metal systems: A review. *Cogent Environ. Scie.* **5** (1), 1, **2019**.
- EZUGBE E.O., RATHILAL S. Membrane Technologies in Wastewater Treatment: A Review. *Membrane*. **10** (5), 89, **2020**.
- SINGH R., HANKINS N., Emerging Membrane technology for Sustainable water treatment, Elsevier, Amsterdam, The Netherlands **2016**.
- PETRINIC I., KORENAK J., POVODNIK D., HELIX-NIELSEN C. A feasibility study of ultrafiltration/reverse osmosis (UF/RO) – based wastewater treatment and reuse in metal finishing industry. *J. Clean. Prod.* **101**, 292, **2015**.
- STEPHANIE M. R., OLIVEIRA J. M. S., REGNERY J., CATH T.Y. Hybrid membrane bio-systems for sustainable treatment of oil and gas produced water and fracturing flow back water. *Sep. Purif. Techn.* **171** (38), 297, **2016**.
- THAÇI S.B., GASHI T.S., Reverse Osmosis Removal of Heavy Metals from Wastewater Effluents Using Biowaste Materials Pretreatment. *Pol. J. Environ. Stud.* **28** (1), 337, **2019**.
- GASHI T. S., DACI N. M., PODVORICA F., SELIMI T., THAÇI S. B. Effect of modification time of coal with aryl diazonium salts on the performance of cellulose acetate-coal heterogeneous reverse osmosis membranes. *Desalination*. **240** (1) 1, **2009**.
- THAÇI S.B., GASHI T.S., PODVORICA F. Preparation of heterogeneous reverse osmosis membranes undergoing modification process. *Des. Water Treat.* **118** (2) 96, **2018**.
- BASU M., GUHA A. K., RAY L. Adsorption of Lead on Cucumber Peel. *J. Clean Prod.* **151** (1), 603, **2017**.