

*Original Research*

# Eco-Friendly Dye of Olive Fruit Peel and Its Color Fastness Applications on Wool/Silk Fabrics

**Amina Asghar<sup>1</sup>, Affifa Tajammal<sup>2</sup>, Salman Ashiq<sup>1,2</sup>, Shabbir Hussain<sup>3\*</sup>,  
Muhammad Ahmad<sup>1</sup>, Kalsoom Sian<sup>1</sup>, Nabil Al-Zaqri<sup>4</sup>, Ahmed Boshala<sup>5,6</sup>,  
Bushra Iqbal<sup>3</sup>, Muhammad Adnan Bodlah<sup>7</sup>**

<sup>1</sup>Department of Chemistry, Division of Science and Technology, University of Education, Lahore-54770, Pakistan

<sup>2</sup>Department of Chemistry, Lahore Garrison University Lahore, Pakistan

<sup>3</sup>Institute of Chemistry, Khwaja Fareed University of Engineering and Information Technology,  
Rahim Yar Khan 64200, Pakistan

<sup>4</sup>Department of Chemistry, College of Science, King Saud University, P.O. Box 2455, Riyadh 11451, Saudi Arabia

<sup>5</sup>Research Centre, Manchester Salt & Catalysis, unit C, 88-90 Chorlton Rd, M15 4AN Manchester, United Kingdom

<sup>6</sup>Libyan Authority for Scientific Research, P. O. Box 80045, Tripoli, Libya

<sup>7</sup>Department of Agricultural Engineering, Khwaja Fareed University of Engineering & Information Technology  
(KFUEIT), Rahim Yar Khan, Punjab, Pakistan

*Received: 6 August 2022*

*Accepted: 28 December 2022*

## Abstract

Most of synthetic dyes are toxic for the environment. On the other hand, natural dyes are eco-friendly and can replace synthetic toxic dyes. In the present studies, a natural dye was extracted from rinsed and grinded olive peel in 1:10 ratio (m/V) with water. Then, fabrics (wool and silk) were dyed with the peel extract by using different types of dulling and shining mordants ( $\text{FeSO}_4$ ,  $\text{CuSO}_4$ ,  $\text{CoSO}_4$ ,  $\text{SnCl}_2$ ,  $\text{K}_2\text{SO}_4$ ,  $\text{Al}_2(\text{SO}_4)_3$ ,  $\text{ZnSO}_4$  and  $\text{NiSO}_4$ ). The mordants have shown best results for wool at the acidic pH (4-5) and for silk at the basic pH (8-9). After dyeing wool (at 70-80°C) and silk (at 100°C) with olive peel extract, by simultaneous mordanting method, an interesting variety of beige, buff and khaki shades were obtained. Color fastness was noted by matching the dyed fabric color with grey scale. The colors of dyed fabric were again noted after its washing, pressing by iron, rubbing and light exposure. The fastness results were found quite satisfactory. The investigated procedure of natural dye extraction is eco-friendly, safe for the environment and a safe technique as it does not involve any organic solvent. The natural dyes can be satisfactory potential substitutes of the synthetic environmentally hazardous dyes.

**Keywords:** olive fruit dye, wool fabric, silk, shades, color fastness

## Introduction

Dyes are intensively colored compounds which are applied to substrates like fiber, cosmetics, paper, hair, etc. to give a specific color [1]. Synthetic dyes are detrimental for health and have some hazardous impacts on the environment as well [2, 3]. Natural dyes have emerged as an eco-friendly solution to the textile industries [4, 5] due to their diverse shades on textile fibers [6] and fabric [7]. They can be extracted from natural resources like plants [8, 9], herbs [10], fungi [11], lichens [1], minerals [12], insects [12] and different tissue cultures of animals [13, 14]. From plant resources, dyes are obtained from their roots, barks [12], leaves [15], berries, fruits [16], flowers [1]. Non-toxicity, non-carcinogenic behavior, renewability, accessibility and non-allergic behavior and bio-degradability are some of the qualities associated with the natural dyes [17]. Natural dyes also demonstrate antimicrobial and medicinal effects [18]. Due to their eco-friendly nature, dyes were extracted from a large number of plant resources and were then applied to textile items [7, 19]. In a study [20], peel of pomegranate was used for the extraction of natural dye which was applied on the cotton by using pre-mordanting, simultaneous-mordanting and post-mordanting substances. Dyes have also been extracted from olive leaves and *Beta vulgaris* for their applications to the textile products [21]. *Rubia cordifolia* contains organic reddish orange dye in its roots, stem and leaves and was used for dyeing of cotton in a study [22]. Research was conducted on the bark of *Macaranga peltata* for yellow color extraction which showed an appreciable color fastness [23]. Natural dye from neem is proved to be efficient in color and has commercial importance [24]. The dyes extracted from mango peel and mango leaves has shown some excellent color fastness values on cotton fabric [25]. Distilled water and alkaline water were used to extract a natural dye from Henna leaves. Alkaline medium extracted dye was found to be more efficient as compared to the distilled water medium. [26]. In another study, colorants were extracted from nine different plants (Cochineal, *Rubia tinctorum*, Alkanna, Henna, Brazil wood, Red sandal, Safflower, Indigo and Logwood) and were then applied to dye cotton and wool fabric by using different mordants [27].

In a nut shell, plants find an important value because of their eco-friendly nature [28, 29], and nutritional [30, 31] and pharmaceutical value [32-34]. *Olea europaea L.* (olive) is a famous commercial crop [35, 36] due to its therapeutic and nutritional potential [37, 38] and is frequently cultivated worldwide including Spain, Italy, Tunisia, Turkey, Greece, Portugal, Morocco, Argentina [35], Iraq [39] etc. The plant contains flavonoids, flavanones, benzoic acid derivatives, iridoids, isochromans and many other metabolites [40]. The natural dye was extracted from the wasted leaves of olive plant and was later applied on cotton fabric to show antibacterial finishing effects [41]. It was also

tested on cotton fabrics woven with handmade yarns by using 3 different mordant materials. The study concluded that dyeing with citric acid mordant (10%) gave the best fastness values [42]. Current studies were performed to develop a method for the extraction of a natural dye from the olive fruit peel. The obtained dye was used for coloring of wool/silk fabrics and its color fastness was also studied. The opted procedure for the extraction of dye is eco-friendly and does not involve an addition of hazardous chemicals. The results show a promising potential of these eco-friendly dyes to replace the synthetic environmentally hazardous dyes.

## Experimental

### Materials

Dried olive peel was obtained from the Sargodha Farmhouse and identified by Department of Biology, Lahore Garrison University Lahore, Pakistan. It was ground for further use. Two kinds of fabric i.e., silk and wool were used for to study the application of that extracted dye. Inorganic mordants i.e., ferrous sulphate, copper sulphate, cobalt sulphate, stannous chloride, potash alum, nickel sulphate and zinc sulphate were supplied by Pakistan Council of Scientific and Industrial Research (PCSIR).

### Extraction of Colorant

Before extraction of natural dye, the chopped olive peel was soaked in water in 1:10 ratio (m/V) for 36-46 h at room temperature. Then, the water and olive oil mixture were boiled for 3-4 hours and filtered with the help of filter paper while hot to obtain the dye extract. The pH was maintained at 8 for silk and 4-5 for wool fabric.

### Dyeing of Fabric

A simultaneous mordanting procedure was used for dyeing the fabrics, where the fabrics were treated with mordants for 45 minutes. The temperature was maintained at 60-80°C for wool dyeing and 100°C to dye the silk fabric. Liquor to goods ratio was 20:1. Extracted dye was used to color the fabrics. After completing the dyeing process of the fabric, these fibers were further processed for testing the fastness and quality of color through washing, light exposure, rubbing and ironing.

## Results and Discussion

A natural dye was extracted from the rinsed and grinded olive peel in 1:10 ratio (m/V) with water. Inorganic mordants (ferrous sulphate, copper sulphate, cobalt sulphate, stannous chloride, potash alum, nickel sulphate and zinc sulphate) were applied to extend

Table 1. Results after light/wash/iron pressing/rubbing treatments of dyed wool/silk.

| Sr. # | Samples           | After light (41°C) exposure for 24 hrs. |      | After washing with water (3 times) |      | After iron pressing |      | After rubbing |     |      |     |     |
|-------|-------------------|---|------|------------------------------------|------|---------------------|------|---------------|-----|------|-----|-----|
|       |                   |   |      |                                    |      |                     |      | Wool          |     | Silk |     |     |
|       |                   | Wool                                    | Silk | Wool                               | Silk | Wool                | Silk | Dry           | Wet | Dry  | Wet |     |
| 1.    | Without mordant   | 4.5                                     | 3.5  | 4.5                                | 4    | 4.5                 | 4.5  | 4.5           | 4.5 | 4.5  | 3   | 4.5 |
| 2.    | Zinc sulphate     | 5                                       | 4    | 3.5                                | 4    | 5                   | 4    | 5             | 5   | 3    | 4.5 | 4.5 |
| 3.    | Ferrous sulphate  | 4.5                                     | 4.5  | 3                                  | 4    | 5                   | 3.5  | 5             | 4.5 | 3.5  | 5   | 5   |
| 4.    | Cobalt sulphate   | 5                                       | 4.5  | 4                                  | 3.5  | 5                   | 4.5  | 3.5           | 3.5 | 3    | 4   | 4   |
| 5.    | Potash alum       | 4.5                                     | 4.5  | 3.5                                | 4    | 4.5                 | 4    | 4.5           | 4.5 | 3.5  | 4   | 4   |
| 6.    | Stannous chloride | 4.5                                     | 4.5  | 4.5                                | 3.5  | 4.5                 | 4.5  | 4.5           | 4.5 | 4    | 4.5 | 4.5 |
| 7.    | Nickel sulphate   | 5                                       | 4    | 3.5                                | 4    | 4.5                 | 4    | 4.5           | 4.5 | 3.5  | 4   | 4   |
| 8.    | Copper sulphate   | 4.5                                     | 4.5  | 3.5                                | 4.5  | 4.5                 | 4.5  | 4.5           | 4.5 | 4    | 4.5 | 4.5 |

the variety of shades. The materials (cotton and wool fabrics) were colored with the brown dye of olive fruit peel. Next, the fabrics were tested for color fastness to exposure of light, iron pressing, rubbing and washing. The colorant was applied on wool and silk with or without mordants and the results were compared. The fastness properties were evaluated by using gray scale which is a scale of shades from black (dark) to white (light). Black and white colors were given arbitrary values of "9" and "1", respectively. This scale measures the intensity of the color or change in intensity of a color after testing. Gray scale measurements are commonly used in imaging and color technology [43]. In general, gray scale is the parameter or tool that measures the variation in color shades after the application of different fastness tests. We compared the color of the fabric with the gray scale before and after dyeing with extracted colorant. The obtained results have been summarized in Table 1 and graphically represented in Fig. 1.

After dyeing the fabric, an interesting variety of beige, buff and khaki shades was obtained. The inorganic mordants (like iron sulphate, stannous chloride, copper sulphate and cobalt sulphate) to extend the variety of shades showed variable results with interesting variety of shades. The mordants develop a kind of bonding with phenolic acids present in the olive fruit peel. Especially, the fabrics dyed in presence of mordants have shown best results for wool at the acidic pH (4-5) and basic pH (8) for wool and silk, respectively. Before evaluating fastness properties, the obtained colors/shades were given arbitrary value of 5 on gray scale. The dyed silk and wool fabrics were subjected to light, iron pressing, rubbing and washing to check the quality, efficiency (fastness) and strength of the extracted dye and the colors/shades were again noted. There were only slight changes (reduction) in colors in few cases where color was faded up to 3.5 as compared to the original 5 value; in most cases the colors remained the same (5 or 4.5) as shown in Table 1.

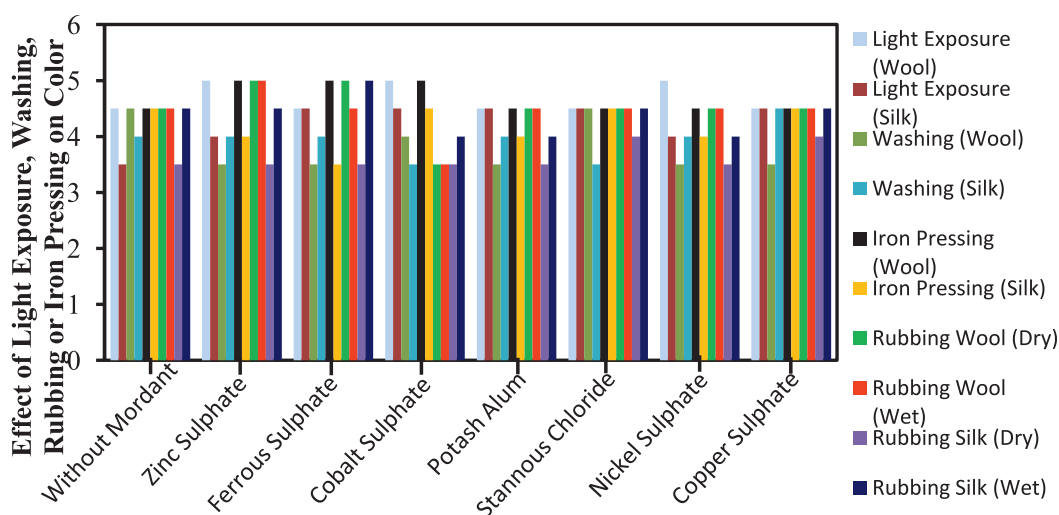


Fig. 1. Graphical representation of color change upon light exposure, washing, rubbing or iron pressing of dyed cloth.

It is obvious from the data that wool and silk are resistant to changes in shades after undergoing different fastness tests. In the presence of investigated mordants (ferrous sulphate, copper sulphate, cobalt sulphate, stannous chloride, potash alum, nickel sulphate and zinc sulphate), the fabric shows almost no change in the gray scale value before and after undergoing fastness tests (Table 1).

It can be demonstrated from Fig. 1 that there were no significant changes in colors/shades even when dyed materials were exposed to sunlight or underwent washing/rubbing/pressing. Moreover, better results are obtained in cases of some mordanted dyed materials as compared to non-mordanted dyed materials. Generally, wool has displayed better results as compared to silk as indicated by nine longest bars out of total nine (longest) in graph (Fig. 1). Superb results were obtained in case of wool dyed in the presence of zinc sulfate, cobalt sulfate and nickel sulfate (mordants), which showed no change in color when it was exposed to sunlight; the fabrics dyed in presence of in the presence of zinc sulfate, cobalt sulfate and ferrous sulfate (mordants) have also shown same kinds of results (outstanding) after iron press testing. As far as, the rubbing fastness results are concerned (Fig. 1, Table 1), dyeing in presence of ferrous sulfate mordant gives exceptional results for dry wool and wet silk whereas dyeing with zinc sulfate mordant gives most superb results for dry wool and wet wool. Current studies demonstrate that olive natural resources potentially find a prodigious worth in textile pigmentation. The ground peel of the olive fruit is an important source of natural dye that can be applied on silk and wool to yield promising results of dye shades; it finds excellent ability to produce stable and persistent brown shades on both kinds of fabric (i.e., wool and silk) in the presence/absence of mordants. In addition, mordants demonstrated very good shades on fabrics.

Natural dye extraction is an eco-friendly safe method. In addition, the natural dyes can be used as antibacterial, decolorizing and UV-protection agents as well as colorants for food products. Many scientific studies have shown that natural dyes are as good as synthetic dyes for coloring purposes [44]. However, they have several advantages over the synthetic dyes because the preparation of synthetic dyes involves the addition of toxic, and hazardous intermediates.

### Conclusions

The olive fruit peel may be used as a good source of natural brown dye for textile pigmentation. The obtained dye can be applied on silk and wool to give them good shades. A simultaneous mordanting dyeing process was used in which different mordants like iron sulphate, stannous chloride, copper sulphate and cobalt sulphate were applied. The mordants have shown appreciable shades on fabrics. The colors of fabrics (wool and silk) are not faded after dyeing them with natural dye from

olive fruit peel even when the dyed material is subjected to prolonged light exposure, washing, pressing by iron and rubbing. The opted procedure is eco-friendly since it does not involve any outside addition of toxic chemicals.

### Acknowledgment

The authors extend their appreciation to the Researchers Supporting Project number (RSP2023R396), King Saud University, Riyadh, Saudi Arabia.

### Conflicts of Interest

The authors declare no conflict of interest.

### References

1. AGGARWAL S. Indian dye yielding plants: Efforts and opportunities. in *Natural Resources Forum*. **2021**. Wiley Online Library.
2. ARDILA-LEAL L.D., POUTOU-PIÑALES R.A., PEDROZA-RODRÍGUEZ A.M., QUEVEDO-HIDALGO B.E. A brief history of colour, the environmental impact of synthetic dyes and removal by using laccases. *Molecules*. **26**, 3813, **2021**.
3. YUSUF M. Synthetic dyes: a threat to the environment and water ecosystem. *Textiles and clothing*. **11**, **2019**.
4. SINGH K., KUMAR P., SINGH N. Natural dyes: an emerging ecofriendly solution for textile industries. *Poll. Res.* **39**, S87, **2020**.
5. FRIED R., OPREA I., FLECK K., RUDROFF F. Biogenic colourants in the textile industry – a promising and sustainable alternative to synthetic dyes. *Green Chem.* **24**, 13, **2022**.
6. AHSAN R., MASOOD A., SHERWANI R., KHUSHBAKHAT H. Extraction and application of natural dyes on natural fibers: an eco-friendly perspective. *R.E.A.L.* **3**, 63, **2020**.
7. EBRAHIM S.A., MOSAAD M.M., OTHMAN H., HASSABO A.G. A Valuable Observation of Eco-friendly Natural Dyes for Valuable Utilisation in the Textile Industry. *J. Text. Color. Polym.* **19**, 25, **2022**.
8. NASEER S., HUSSAIN S., ABID A. Betalain as a Food Colorant: its Sources, Chemistry and Health Benefits: Chemistry of Betalain and its Role as Food Colorant. *Proc. Pak. Acad. Sci.: B.* **56**, 01, **2019**.
9. NASEER S., AFZAL M., NISA A., HUSSAIN S., AHMAD M., PARVEEN S., ANJUM F., RIAZ M. Extraction of brown dye from Eucalyptus bark and its applications in food storage. *Qual. Assur. Saf. Crop. Foods*, **11**, 769, **2019**.
10. ADEEL S., ZIA K.M., ABDULLAH M., REHMAN F.-U., SALMAN M., ZUBER M. Ultrasonic assisted improved extraction and dyeing of mordanted silk fabric using neem bark as source of natural colourant. *Nat. Prod. Res.* **33**, 2060, **2019**.
11. HINSCH E.M., WEBER G., CHEN H.-L., ROBINSON S.C. Colorfastness of extracted wood-staining fungal

- pigments on fabrics: A new potential for textile dyes. J. Text. Appar. Technol. Manag. **9**, 2015.
12. GÜRSES A., AÇIKYILDI Z. M., GÜNEŞ K., GÜRSES M.S., Historical development of colorants, in Dyes and pigments. Springer. p. 1, 2016.
  13. BAFANA A., DEVI S.S., CHAKRABARTI T. Azo dyes: past, present and the future. Environ. Rev. **19**, 350, 2011.
  14. SIVA R. Status of natural dyes and dye-yielding plants in India. Curr. Sci. **92**, 916, 2007.
  15. SINGH R., SRIVASTAVA S. A critical review on extraction of natural dyes from leaves. Int. J. Home Sci. **3**, 100, 2017.
  16. MARISELVAM R., RANJITSINGH A., MOSAE SELVAKUMAR P., KRISHNAMOORTHY R., ALSHATWI A.A. Eco friendly natural dyes from *Syzygium cumini* (L) (Jambolan) fruit seed endosperm and to preparation of antimicrobial fabric and their washing properties. Fibers Polym. **18**, 460, 2017.
  17. ROTICH KIPKOECH V., Preparation and characterization of beta vulgaris peels and pomace dye extracts as a potential natural dye of Cotton Fabric. 2021, Moi University.
  18. ONAL A., ESER F., BAYRAK S. Investigation of Dyeing properties of different fabric species with *Alkanna orientalis* root extract. J. Food Sci. Eng. **7**, 1, 2017.
  19. JIANG H., GUO R., MIA R., ZHANG H., LÜ S., YANG F., MAHMUD S., LIU H. Eco-friendly dyeing and finishing of organic cotton fabric using natural dye (gardenia yellow) reduced-stabilized nanosilver: full factorial design. Cellulose. **29**, 2663, 2022.
  20. KULKARNI S., GOKHALE A., BODAKE U., PATHADE G. Cotton Dyeing with Natural Dye Extracted from Pomegranate (*Punica granatum*) Peel. Univers. J. Environ. Res. Technol. **1**, 135, 2011.
  21. AL-KHATEEB D.S.M. Extraction Dyes From Two Natural Plants Olive Leaves and *Beta vulgaris* And The Uses In dyeing Textile. in Journal of Physics: Conference Series. 2019. IOP Publishing.
  22. VANKAR P.S., SHANKER R., MAHANTA D., TIWARI S. Ecofriendly sonicator dyeing of cotton with *Rubia cordifolia* Linn. using biomordant. Dyes Pigm. **76**, 207, 2008.
  23. VINOD K.N., NINGE GOWDA K.N., SUDHAKAR R. Natural colorant from the bark of *Macaranga peltata*: kinetic and adsorption studies on silk. Color. Technol. **126**, 48, 2010.
  24. BUKHARI H., HEBA M., KHADIJAH Q. Ecofriendly dyeing textiles with Neem herb for multifunctional fabrics. Part 1: Extraction standardization. Int. J. Tech. Res. App. **2**, 51, 2014.
  25. AYELE M., TESFAYE T., ALEMU D., LIMENEH M., SITHOLE B. Natural dyeing of cotton fabric with extracts from mango tree: A step towards sustainable dyeing. Sustain. Chem. Pharm. **17**, 100293, 2020.
  26. ALI S., HUSSAIN T., NAWAZ R. Optimization of alkaline extraction of natural dye from Henna leaves and its dyeing on cotton by exhaust method. J. Clean. Prod. **17**, 61, 2009.
  27. ZARKOGIANNI M., MIKROPOULOU E., VARELLA E., TSATSARONI E. Colour and fastness of natural dyes: revival of traditional dyeing techniques. Color. Technol. **127**, 18, 2011.
  28. RASHEED R.B., HUSSAIN S., SYED S.K. Phytochemistry, nutritional and medicinal value of kiwi fruit. Postepy Biol. Komorki. **48**, 147, 2021.
  29. SIDDIQUA A., HUSSAIN S., SYED S.K. Phytochemistry, Nutritional and Medicinal Importance of Almond. Postepy Biol. Komorki. **48**, 167, 2021.
  30. FARHAT N., HUSSAIN S., SYED S.K., AMJAD M., JAVED M., IQBAL M., HUSSAIN M., HAROON S.M., RAZA H., BUTT S.Z. Dietary phenolic compounds in plants: Their antioxidant and pharmacological potential. Postepy Biol. Komorki. **47**, 307, 2020.
  31. HUSSAIN S., JAVED M., ABID M.A., KHAN M.A., SYED S.K., FAIZAN M., FERAZ F. *Prunus Avium* L.; Phytochemistry, Nutritional and Pharmacological Review. Adv. Life Sci. **8**, 307, 2021.
  32. RIAZ M., FATIMA H., UR REHMAN M.M., QADIR R., HUSSAIN S., HAFEEZ A., SIDDIQUE A.B. Appraisal of antioxidant potential and biological studies of bogan bail (*Bougainvillea glabra*) leaf extracts using different solvents. Czech J. Food Sci. **39**, 176, 2021.
  33. RIAZ M., SAQLAIN R., HUSSAIN S., AFZAL M., QADIR R. Antidiabetic, Thrombolytic, Antimicrobial, Antioxidant and Cytotoxicity Studies of Brinjal (*Solanum Melongena*) Leaves Extracts. LGU J. Life Sci. **5**, 76, 2021.
  34. NASEER S., HUSSAIN S., NAEEM N., PERVAIZ M., RAHMAN M. The phytochemistry and medicinal value of *Psidium guajava* (guava). Clin. Phytoscience. **4**, 1, 2018.
  35. MALÉCHAUX A., LE DRÉAU Y., ARTAUD J., DUPUY N. Exploring the scientific interest for olive oil origin: a bibliometric study from 1991 to 2018. Foods. **9**, 556, 2020.
  36. KASHIWAGI K., ERRAACH Y., ARFA L., ZAIBET L. Growing olive oil export and intra-industry trade in Mediterranean countries: Application of gravity model. Sustainability. **12**, 7027, 2020.
  37. KHALIQ A., ALI SHAH S.M., AKRAM M., MUNIR N., DANİYAL M., IRSHAD M., AHMAD S. Determination of oil contents from eight varieties of *Olea europaea* (Olive) grown in Pakistan. Nat. Prod. Res. **34**, 1951, 2020.
  38. JULCA I., MARCET-HOUBEN M., CRUZ F., GÓMEZ-GARRIDO J., GAUT B.S., DíEZ C.M., GUT I.G., ALIOTO T.S., VARGAS P., GABALDÓN T. Genomic evidence for recurrent genetic admixture during the domestication of Mediterranean olive trees (*Olea europaea* L.). BMC Biol. **18**, 1, 2020.
  39. NAJIM EL-DDIN S., HALEEM R.A. First record of *Dactylonectria macrodidyma*: A cause of olive root rot in Iraq. Forest Pathology. **52**, e12729, 2022.
  40. MORSY M.K., SAMI R., ALGARNI E., AL-MUSHHIN A.A., BENAJIBA N., ALMASOUDI A.G., MEKAWI E. Phytochemical Profile and Antioxidant Activity of Sesame Seed (*Sesamum indicum*) By-Products for Stability and Shelf Life Improvement of Refined Olive Oil. Antioxidants. **11**, 338, 2022.
  41. YILMAZ F., BAHTIYARI M.İ. Antibacterial finishing of cotton fabrics by dyeing with olive tree leaves fallen during olive harvesting. J. Clean. Prod. **270**, 122068, 2020.
  42. ÖZOMAY M., GÜNGÖR F., ÖZOMAY Z. Determination of optimum dyeing recipe with different amount of mordants in handmade cotton fabrics woven with olive leaves by grey relational analysis method. J. Text. Inst. **113**, 1048, 2022.
  43. WAN S., XIA Y., QI L., YANG Y.-H., ATIQUZZAMAN M. Automated colorization of a grayscale image with seed points propagation. IEEE Trans. Multimed. **22**, 1756, 2020.
  44. MIRJALILI M., NAZARPOOR K., KARIMI L. Eco-friendly dyeing of wool using natural dye from weld as co-partner with synthetic dye. J. Clean. Prod. **19**, 1045, 2011.

