

Original Research

# Green Synthesis of NiO Nanoparticles Using the Shell Waste of *Prunus dulcis*: their Characterization and Electrochemical Studies

Waqar Mirza<sup>1</sup>, Shabbir Hussain<sup>2\*</sup>, Affifa Tajammal<sup>1</sup>, Amina Asghar<sup>3</sup>, Bushra Parveen<sup>4</sup>,  
Tauqeer Ahmad<sup>5,6</sup>, Farzana Shaheen<sup>7</sup>, Zeeshan Mustafa<sup>8\*\*</sup>, Mohammad Z. Ahmed<sup>9</sup>,  
Amjad Islam<sup>10</sup>

<sup>1</sup>Department of Chemistry, Lahore Garrison University, Lahore, Pakistan

<sup>2</sup>Institute of Chemistry, Khwaja Fareed University of Engineering and Information Technology,  
Rahim Yar Khan 64200, Pakistan

<sup>3</sup>Department of Chemistry, Division of Science and Technology, University of Education, Lahore-54770, Pakistan

<sup>4</sup>Department of Physics, Rawalpindi Women University, Satellite Town, Rawalpindi, Pakistan

<sup>5</sup>Institute of Chemistry, University of Sargodha, 40100, Pakistan

<sup>6</sup>Department of Chemistry, University of Mianwali, 42200, Pakistan

<sup>7</sup>Department of Chemistry, Allama Iqbal Open University, 44310 Islamabad, Pakistan

<sup>8</sup>Department of Physics, Lahore Garrison University Lahore, Pakistan

<sup>9</sup>Department of Pharmacognosy, College of Pharmacy, King Saud University, Riyadh 11451, Saudi Arabia

<sup>10</sup>Key Laboratory for Preparation and Application of Ordered Structured Materials of Guangdong Province,  
College of Chemistry and Chemical Engineering, Shantou University, Shantou, Guangdong Province, China

Received: 7 November 2023

Accepted: 12 March 2024

## Abstract

Nickel oxide (NiO) nanoparticles (NPs) were successfully synthesized by utilizing the waste shell powder of *Prunus dulcis* (almond) through a simple, environmentally sound, cheap, and novel green approach. The almond shell powder was used as a stabilizing and reducing agent for the synthesis of NiO nanoparticles from NiNO<sub>3</sub>.6H<sub>2</sub>O solution at 60 °C and pH 12. FTIR studies verified the synthesis of NiO NPs by the appearance of a characteristic vibrational peak at 611.97cm<sup>-1</sup> whereas an absorption peak at 267 nm appeared in the UV-Visible spectrum. However, the XRD and SEM analyses have shown the amorphous nature of synthesized NiO NPs. The cyclic voltammetry (CV) curve of NPs clearly indicated the redox reaction and the reversible behavior of NiO NPs. The galvanostatic charge discharge (GCD) curves have shown a higher charging time as compared to the discharging time.

**Keywords:** Biosynthesis, NiO, almond shell powder, cyclic voltammetry, GCD

\*e-mail: shabchem786@gmail.com;

\*\*e-mail: zeeshanmustafa@lgu.pk

## Introduction

Nanotechnology plays an important role in different disciplines of life [1], including water treatment [2], biomedical services [3], drug delivery [4], photo-electrochemical applications, catalysis [5], cosmetics [6], optics [7], etc. Currently, the green synthetic methodology is a fast-growing approach that involves the use of numerous organisms or plants for the synthesis of NPs [8]. Biocompatibility, cost effectiveness, and many other factors are driving the green production of NiO NPs [9]. Moreover, this method is rapid, more secure, eco-friendly, sustainable, and is associated with many ecological benefits [10, 11]. NiO-NPs were reported earlier owing to their clinical and catalytic applications, enzyme inhibition, remediation, antioxidant, anticancer, cytotoxic, antifungal, and antibacterial properties [12]. They are highly reactive and eco-friendly and are employed in magnetic separations [13], automatic catalytic converters, magnetic fluids, propellants, and sintering additives, fast separations [13], and the absorption of inorganic pollutants and harmful dyes [14]. They are used in optoelectronic devices as catalysts for benzyl alcohol oxidation [15]. Because of their smaller size (4.5 nm diameter) and large surface area, NiO NPs have shown good electrical activity and were reported as an electrode material in super capacitors [16]. Nickel nanoparticles (NPs) have the potential to be used in a variety of fields, such as biomedicine [17], magnetism [18], electronics [19], and energy technology [20]. They are used to catalyze a variety of organic reactions, such as the reduction of aldehydes and ketones [21], the hydrogenation of olefins [22], the synthesis of stilbenes from alcohol through Wittig-type olefination [23], the alkylation of methyl ketone [24], and also for photocatalytic hydrogen evaluation by using an aqueous methanol solution [25]. NiO NPs capped with biomolecules like glucose demonstrate significantly increased biocompatibility, making them useful as biosensors and heat nonmediators for cancer hyperthermia [26].

Currently, plant-mediated synthesis of NPs has attracted the attention of researchers due to its cost-effectiveness, sustainability, and useful applications [27, 28]. Plants have been considered important sources for green synthesis due to their easy availability [29] and useful phytochemical ingredients [30, 31]. The almond (also known as *Prunus dulcis*, *Prunus amygdalus*, or *Amygdalus communis*) is a tiny deciduous tree that relates to the Rosaceae subfamily *Prunoideae* and bears an almond-like fruit [32]. Kernel, hull, and shell are three components of almonds [33]. The edible portion of the nut is the kernel. Almond shells are totally contained in about  $\frac{3}{4}$  portion of total almond fruit. The shell is the central portion of the external kernel and hull. Hemi-cellulose, cellulose, and starch make up the majority of the almond shell; the ratio between these components determines the strength of the shell [34]. After the use of the kernel (edible portion) of an

almond, its shell (not edible) is discarded as waste material.

The primary goal of this research is to utilize the waste shell material of *Prunus dulcis* (almond) for the synthesis of nickel oxide nanoparticles through a green route. The synthesized NPs have been characterized by XRD, FTIR, UV-Visible, and SEM analyses, and they were also subjected to electrochemical studies by cyclic voltammetry and galvanostatic charge-discharge (GCD) testing.

## Materials and Methods

Nickel (II) nitrate 6-hydrate, sodium hydroxide, and methanol were used in this study; they were purchased from Sigma Aldrich and were used without further purification. The powder extract of *Prunus dulcis* shell (a waste material) was used as a reducing agent. A Bruker AXS, D8 Advance X-ray diffractometer (XRD) instrument was used to analyze the structural information of JSM-6480LV. The synthesized NPs were tested for their optical properties by using a UV-Visible Spectrophotometer (UVD-3500, Lambod, Inc., UAS, Double Beam). The functional group analysis was performed with an FT-IR Spectrometer (Cary 630, Agilent Technology, USA). The electrochemical applications of NiO NPs were determined from Cyclic Voltammetry (CV) by Potentiostat/Galvanostat of model CS300.

### Green Synthesis of Ni Nanoparticles by Using *Prunus dulcis* Shell Powder Extract

#### *Preparation of Plant Extract*

*Prunus dulcis* (almond) with shells (Fig. 1a) were purchased from a local market in Lahore, Punjab, Pakistan, in August 2022. The *Prunus dulcis* shells (Fig. 1b) were washed with distilled water to remove dirt and contaminants and dried at 80°C for 4 hours, then the almond shells were ground by a steel grinder into a homogenized almond shell powder (Fig. 1c). 30 g of *Prunus dulcis* shell powder was soaked in 100 mL of 40% methanol. The solution was stirred for 24 hours at ambient temperature. The extract was filtered, centrifuged to remove any impurities, and refrigerated at 4°C for its usage within a week.

#### *Procedure for the Synthesis of Ni Nanoparticles*

30 mL of 5% nickel (II) nitrate hexa-hydrate was taken in a 250 mL beaker. Then 30 mL of almond shell extract was added to it, and the pH of the solution was maintained at 12 by adding a drop-wise NaOH solution (0.1 N). The solution was stirred for 2 hours at 60°C, cooled, and centrifuged at 2000 rpm for 15 minutes at ambient temperature. The color of the solution was changed from dark green to light green, confirming the

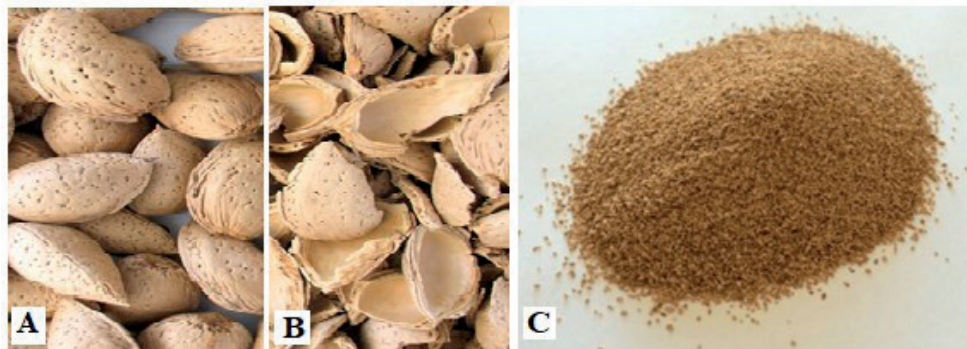


Fig. 1. a) *Prunus dulcis* (almond with shells) b) Broken shells of *Prunus dulcis* after separation of its seeds (nuts) c) Fine powder of *Prunus dulcis* shells.

synthesis of NiO NPs. The solution was finally filtered, and the obtained nanoparticles (residue) were dried in an oven at 100°C; finally, they were stored for analysis and further usage.

## Results and Discussion

### FT-IR Spectroscopy

The FTIR spectrum of the synthesized nanomaterials was recorded in the range of 4000-500  $\text{cm}^{-1}$ ; the obtained spectrum has been shown in Fig. 2. The different peaks could be interpreted as representatives of the vibrational modes of the nanoparticle. The spectrum has shown a very clear Ni-O vibrational stretch of medium intensity at 611.97  $\text{cm}^{-1}$ . The C-O bond stretching band was reflected by the large absorption peak at 1344.25  $\text{cm}^{-1}$ , whereas a peak at 1625.97  $\text{cm}^{-1}$  existed due to the C=O group of the carbonyl group. The stretching bands at a frequency of 3368.37  $\text{cm}^{-1}$  were attributed to

the presence of O-H groups. The simultaneous existence of C-O, C=O, and O-H peaks evidently depicts the presence of carboxylic acid moieties on the surface of the synthesized NPs. It commonly occurs in plant-mediated NP synthesis, where the plant material acts as a coating on the surface of NPs and also prevents their agglomeration.

### UV-Visible Spectroscopy

UV-Visible spectroscopy is a very important tool for the verification of NiO-NPs. The formation of synthesized NPs can be verified by measuring the highest absorption peak and analyzing the collective oscillations of conduction band electrons in response to the electromagnetic pulses. UV-Visible spectroscopy (Fig. 3) has shown a maximum absorption band at 267 nm, which verified the presence of NiO NPs (Ikuhara al., 2012).

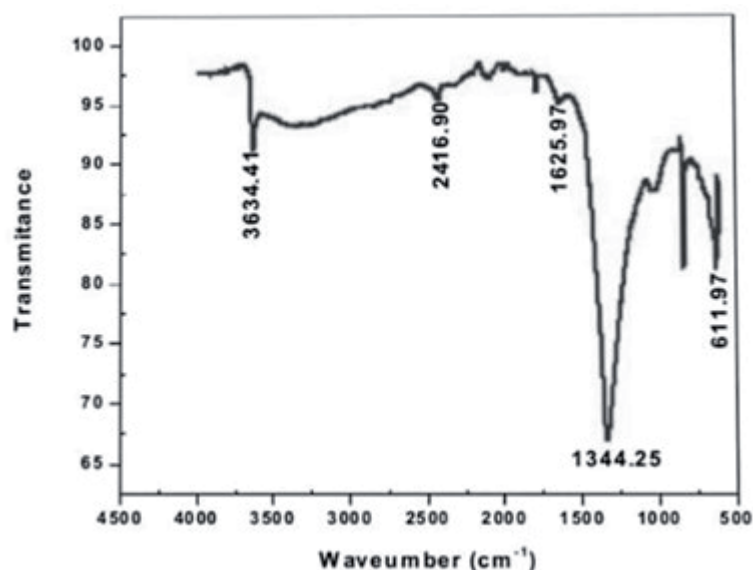


Fig. 2. FTIR spectrum of the synthesized NPs.

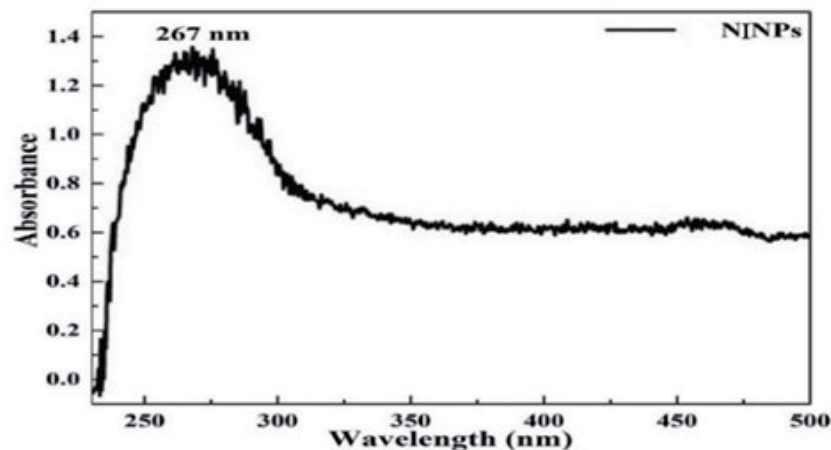


Fig. 3. UV-Visible spectrum of NiO NPs.

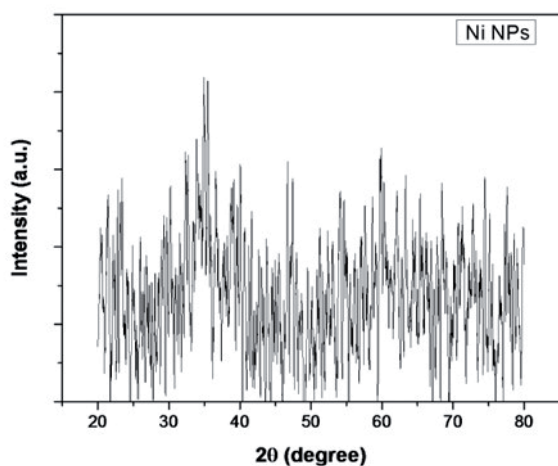


Fig. 4. XRD picture of synthesized NiO NPs.

### Structural Studies

X-ray powder diffraction (XRD) is typically employed for characterizing crystalline materials and can yield data on the dimensions of their unit cells. Analyzing X-ray diffraction (XRD) data carefully can provide valuable information and also assist in

correlating microscopic findings with the bulk sample because XRD patterns seem different for specimens of nanomaterials having varying shapes and sizes. The XRD spectra of the synthesized NPs were recorded between  $2\theta$  values of 10 and  $80^\circ$ ; the respective patterns are shown in Fig. 4. The XRD patterns have shown no distinct peak for NiO nanoparticles, demonstrating the amorphous nature of the synthesized material. So, it was not possible to determine the crystallite size due to its amorphous nature, which is also verified from the SEM images (next section). Here, almond shell powder acts as a stabilizer or capping agent, demonstrating the amorphous behavior of nickel nanoparticles. This might be due to the low-temperature synthesis method (ImranDin, 2016).

### SEM Analysis

A scanning electron microscope (SEM) was used to investigate the morphology of synthesized NPs. The obtained SEM images of NiO NPs at  $50\ \mu\text{m}$  and  $100\ \mu\text{m}$  are shown in Fig. 5.

The SEM results completely support the findings of the XRD analysis, as discussed in the last section. Since XRD studies confirmed the amorphous nature of synthesized NiO-NPs, it was not possible to determine

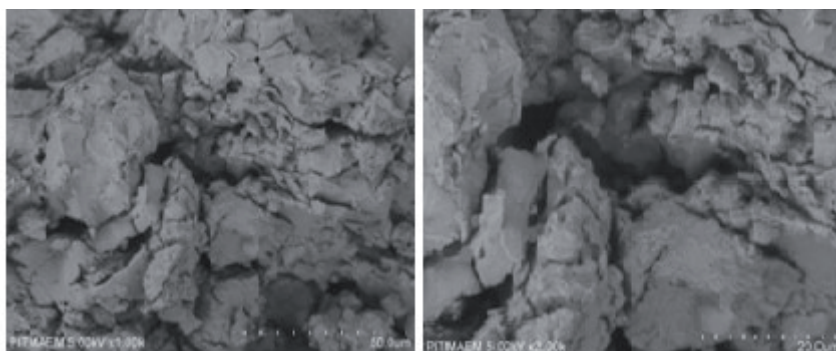


Fig. 5. SEM images of NiO-NPs at  $50\ \mu\text{m}$  (Left) and  $100\ \mu\text{m}$  (Right).

their morphology and size. The results indicated that nickel nanoparticles are amorphous in nature.

### Electrochemical Studies of NiO NPs

#### *Cyclic Voltammetry*

The kinetic irreversibility of the redox reaction causes an asymmetry between the oxidation and reduction peaks throughout the anodic and cathodic scans. The cyclic volta-gram of the synthesized NPs is shown in Fig. 6. As with the cathodic scan, the  $\text{Ni}^{2+}$  in the KOH electrolyte is oxidized to  $\text{Ni}^{3+}$  during the scanning of the anode from  $-1.000$ - $1.000$  V. In the presence of an electrical field, ions migrate across the electrolytic solution to the NiO electrode. Since the electrolyte does not transport electrons, it prevents the transfer of charge-

neutralizing electrons across the electrolyte. In this way, electrons from an external circuit infiltrate into the electrode material, where they mix with surface-bound ions. Therefore, the electrochemical reaction takes place close to the NiO electrode's surface.

The observed redox potential of NiO NPs was  $0.0892$  V at a scan rate of  $100 \text{ mVs}^{-1}$ , whereas the redox current was found to be  $1.0284 \text{ mA}$ .

#### *Galvanostatic Charge and Discharge (GCD)*

The GCD curve (Fig. 7) showed the charging and discharging peaks of NiO NPs. The charging capacitance is  $13.924$ ,  $61.32$ ,  $18.95$ ,  $2.411$ , and  $7.620$  at an applied current of  $1, 2, 3, 4$ , and  $5 \text{ A}$ . Moreover, the discharging capacitance is  $1.369$ ,  $0.746$ ,  $0.746$ ,  $2.614$ ,  $1.169$ , and  $2.260$  at the applied current.

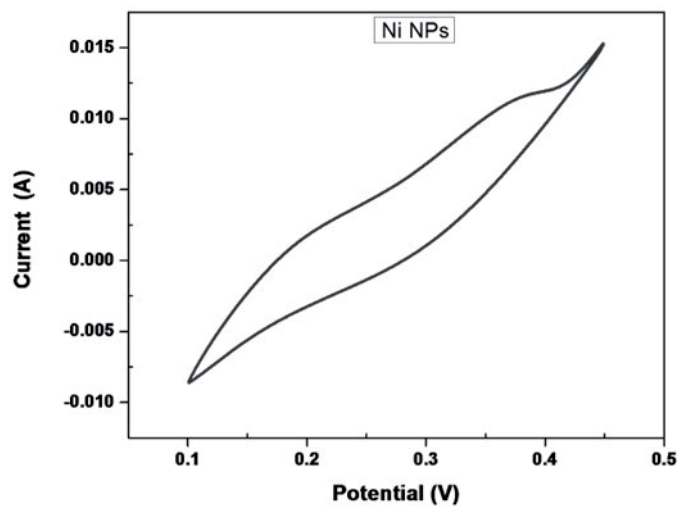


Fig. 6. Cyclic Volta-gram of the synthesized Ni-O NPs.

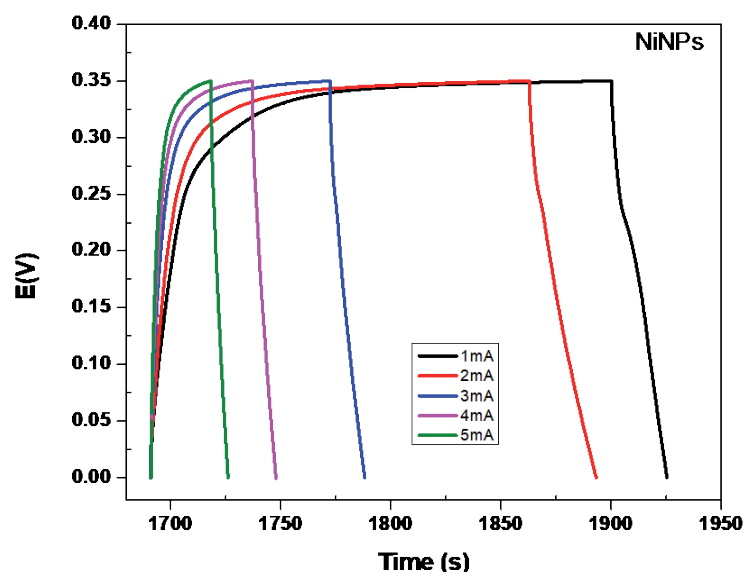


Fig. 7. GCD curve of the synthesized Ni-O NPs.

showed that charging time is greater than discharging, which demonstrated that NPs are good irreversible materials.

### Conclusion

Nickel oxide (NiO) nanoparticles were successfully synthesized by treating  $\text{NiNO}_3 \cdot 6\text{H}_2\text{O}$  with the waste shell powder of *Prunus dulcis* (almond) and using a simple, environmentally sound, cheap, and novel green approach. FTIR and UV-Visible spectroscopies verified the formation of Ni-O nanoparticles. However, XRD and SEM analyses demonstrated the amorphous nature of NPs. There was a coating of carboxylic acid moieties on the surface of the NPs. The electrochemical studies were performed by cyclic voltammetry and GCD. Cyclic voltammetry has shown the redox nature of the synthesized NiO NPs. The charging time of the synthesized nickel oxide NPs was higher as compared to the discharging time.

### Acknowledgments

The authors are grateful to the Researchers Supporting Project number (RSPD2024R728), King Saud University, Riyadh, Saudi Arabia.

### Conflict of Interest

The authors declare no conflict of interest

### References

- MCNEIL S.E. Nanotechnology for the biologist. *Journal of Leukocyte Biology*, **78** (3), 585, **2005**.
- REHMAN H., ALI Z., HUSSAIN M., GILANI S., SHAHZADI T., ZAHRA A., HUSSAIN S., HUSSAIN H., HUSSAIN I., FAROOQ M. Synthesis and characterization of ZnO nanoparticles and their use as an adsorbent for the arsenic removal from drinking water. *Digest Journal of Nanomaterials and Biostructures*, **14** (4), 1033, **2019**.
- NOSHEEN S., IRFAN M., ABIDI S.H., SYED Q., HABIB F., ASGHAR A., WASEEM B., SOOMRO B., BUTT H., AKRAM M. A review: Development of magnetic nano vectors for biomedical applications. *GSC Advanced Research and Reviews*, **8** (2), 085, **2021**.
- ZULFIQAR H. Nature of nanoparticles and their applications in targeted drug delivery. *Pakistan Journal of Science*, **72** (1), 30, **2020**.
- JAVED M., ABID M., HUSSAIN S., SHAHWAR D., ARSHAD S., AHMAD N., ARIF M., KHAN H., NADEEM S., RAZA H. Synthesis, characterization and photocatalytic applications of s-doped graphitic carbon nitride nanocomposites with nickel doped zinc oxide nanoparticles. *Digest Journal of Nanomaterials and Biostructures*, **15**, 1097, **2020**.
- KING M.F.L., NITHYA S.S. Applications of Nanoparticles in the Cosmetic Field. In *Sustainable Utilization of Nanoparticles and Nanofluids in Engineering Applications*, IGI Global: pp.102, **2023**.
- HASSAN N.K., KHALID F.G., EKSHAYESH A.A., IBRAHIM R.K., SALIM E.T., FAKHRI M.A., ABDULWAHHAB A.W., ALSULTANY F.H., GOPINATH S.C., DAHHAM O.S. Optical investigations of gold nano rods and gold nano rods doped with ZnO nanoparticles for optoelectronic applications. *Journal of Optics*, **1**, **2023**.
- BARAKAT A., AL-NOAIMI M., SULEIMAN M., ALDWAYYAN A.S., HAMMOUTI B., BEN HADDA T., HADDAD S.F., BOSHAALA A., WARAD I. One step synthesis of NiO nanoparticles via solid-state thermal decomposition at low-temperature of novel aqua (2, 9-dimethyl-1, 10-phenanthroline)  $\text{NiCl}_2$  complex. *International Journal of Molecular Sciences*, **14** (12), 23941, **2013**.
- MOODLEY J.S., KRISHNA S.B.N., PILLAY K., GOVENDER P. Green synthesis of silver nanoparticles from *Moringa oleifera* leaf extracts and its antimicrobial potential. *Advances in Natural Sciences: Nanoscience and Nanotechnology*, **9** (1), 015011, **2018**.
- ASGHAR A., MABARAK S., ASHRAF B., RIZWAN M., MASSEY S., ASGHAR B.H., SHAHID B., RASHEED T. A sustainable approach for the removal of chlorpyrifos pesticide from aqueous phase using novel nano magnetized biochar. *Inorganic Chemistry Communications*, **159**, 111790, **2024**.
- RIAZ T., ASGHAR A., SHAHZADI T., SHAHID S., MANSOOR S., ASGHAR A., JAVED M., IQBAL S., ALOTAIBI M.T., ALTHOBITI R.A. Green synthesis of ZnO and Co-ZnO using *Brassica rapa* leave's extract and their activities as antioxidant agents, efficient adsorbents, and dye removal agents. *Journal of Saudi Chemical Society*, **27** (5), 101716, **2023**.
- SANA S.S., SINGH R.P., SHARMA M., SRIVASTAVA A.K., MANCHANDA G., RAI A.R., ZHANG Z.-J. Biogenesis and application of nickel nanoparticles: A review. *Current Pharmaceutical Biotechnology*, **22** (6), 808, **2021**.
- SIMONSEN G., STRAND M., ØYE G. Potential applications of magnetic nanoparticles within separation in the petroleum industry. *Journal of Petroleum Science and Engineering*, **165**, 488, **2018**.
- PANDIAN C.J., PALANIVEL R., DHANANASEKARAN S. Green synthesis of nickel nanoparticles using *Ocimum sanctum* and their application in dye and pollutant adsorption. *Chinese journal of Chemical engineering*, **23** (8), 1307, **2015**.
- SUDHASREE S., SHAKILA BANU A., BRINDHA P., KURIAN G.A. Synthesis of nickel nanoparticles by chemical and green route and their comparison in respect to biological effect and toxicity. *Toxicological & Environmental Chemistry*, **96** (5), 743, **2014**.
- XU C., LEI C., YU C. Mesoporous silica nanoparticles for protein protection and delivery. *Frontiers in Chemistry*, **7**, 290, **2019**.
- MARIAM A.A., KASHIF M., AROKIYARAJ S., BOUODINA M., SANKARACHARYULU M., JAYACHANDRAN M., HASHIM U. Bio-synthesis of NiO and Ni nanoparticles and their characterization. *Digest Journal of Nanomaterials and Biostructures*, **9** (3), 1007, **2014**.
- VENKATALAKSHMI N., KINI H.J., NAIK H.B. Green-synthesized Nickel oxide nanoparticles: Magnetic and biomedical applications. *Inorganic Chemistry Communications*, **151**, 110490, **2023**.

19. UMARBEEK A., VAXITOVICH A., RAXIMOVA Y., KARABAYEVA M., SAIDKULOV D., MATYAKUBOV B. An Investigation of the Electrophysical Properties of Composite Ceramic Materials Containing Nickel Nanoparticles. *Physical Chemistry Research*, **11** (2), 231, **2023**.
20. TAMADONI SARAY M., YURKIV V., SHAHBAZIAN-YASSAR R. Role of Kinetics and Thermodynamics in Controlling the Crystal Structure of Nickel Nanoparticles Formed on Reduced Graphene Oxide: Implications for Energy Storage and Conversion Applications. *ACS Applied Nano Materials*, **6** (12), 10033, **2023**.
21. MUTHUVINOTHINI A., STELLA S. Surface modified nanoparticles: a green catalyst for the reduction of ketones. *Inorganic and Nano-Metal Chemistry*, **52** (3), 397, **2022**.
22. AVELLO M.G., GOLLING S., TRUONG-PHUOC L., VIDAL L., ROMERO T., PAPAETHIMIOU V., GRUBER N., CHETCUTI M.J., LEROUX F.R., DONNARD M. (NHC-olefin)-nickel (0) nanoparticles as catalysts for the (Z)-selective semi-hydrogenation of alkynes and ynarnides. *Chemical Communications*, **59** (11), 1537, **2023**.
23. ALONSO F., RIENTE P., YUS M. Wittig-Type Olefination of Alcohols Promoted by Nickel Nanoparticles: Synthesis of Polymethoxylated and Polyhydroxylated Stilbenes. *Wiley Online Library*, **2009**.
24. ALONSO F., RIENTE P., YUS M. Alcohols for the  $\alpha$ -Alkylation of Methyl Ketones and Indirect Aza-Wittig Reaction Promoted by Nickel Nanoparticles. *Wiley Online Library*, **2008**.
25. AGEENEHU A.K., PAN C.-J., RICK J., LEE J.-F., SU W.-N., HWANG B.-J. Enhanced hydrogen generation by cocatalytic Ni and NiO nanoparticles loaded on graphene oxide sheets. *Journal of Materials Chemistry*, **22** (27), 13849, **2012**.
26. VASEEM M., TRIPATHY N., KHANG G., HAHN Y.-B. Green chemistry of glucose-capped ferromagnetic hcp-nickel nanoparticles and their reduced toxicity. *RSC Advances*, **3** (25), 9698, **2013**.
27. HUSSAIN S., ALI MUAZZAM M., AHMED M., AHMAD M., MUSTAFA Z., MURTAZA S., ALI J., IBRAR M., SHAHID M., IMRAN M. Green synthesis of nickel oxide nanoparticles using *Acacia nilotica* leaf extracts and investigation of their electrochemical and biological properties. *Journal of Taibah University for Science*, **17** (1), 2170162, **2023**.
28. HUSSAIN S., AZIZ I., WAQAS M., AHMAD T., AHMAD I., TAHIR M.B., AL HUWAYZ M., ALWADAI N., IQBAL M., NAZIR A. Potential Antifungal and Antimicrobial Effects of Nano Zinc Oxide Particles Obtained from *Cymbogobon citratus* Leaf Extract Using Green Technology. *Polish Journal of Environmental Studies*, **32** (5), 4065, **2023**.
29. YASMEEN G., HUSSAIN S., TAJAMMAL A., MUSTAFA Z., SAGIR M., SHAHID M., IBRAR M., ELQAHTANI Z.M., IQBAL M. Green Synthesis of Cr<sub>2</sub>O<sub>3</sub> Nanoparticles by *Cassia Fistula*, their Electrochemical and Antibacterial Potential. *Arabian Journal of Chemistry*, **16**, 104912, **2023**.
30. HUSSAIN S., JAVED W., TAJAMMAL A., KHALID M., RASOOL N., RIAZ M., SHAHID M., AHMAD I., MUHAMMAD R., SHAH S.A.A. Synergistic Antibacterial Screening of *Cymbopogon citratus* and *Azadirachta indica*: Phytochemical Profiling and Antioxidant and Hemolytic Activities. *ACS Omega*, **8** (19), 16600, **2023**.
31. MAHMOOD N., MUAZZAM M.A., AHMAD M., HUSSAIN S., JAVED W. Phytochemistry of *Allium cepa* L. (Onion): An Overview of its Nutritional and Pharmacological Importance. *Scientific Inquiry and Review*, **5** (3), 41, **2021**.
32. MITRA S., SERÇE Ç.U., GAZEL M., UN NABI S., ZAMHARIR M.G., RAO G.P. Updates on phytoplasma diseases associated with fruit crops in Asia. In *Phytoplasma Diseases of Major Crops, Trees, and Weeds*, Elsevier: pp. 45, **2023**.
33. BARRECA D., NABAVI S.M., SUREDA A., RASEKHIAN M., RACITI R., SILVA A.S., ANNUNZIATA G., ARNONE A., TENORE G.C., SÜNTAR I. Almonds (*Prunus dulcis* Mill. DA webb): A source of nutrients and health-promoting compounds. *Nutrients*, **12** (3), 672, **2020**.
34. FRANKLIN L.M., MITCHELL A.E. Review of the sensory and chemical characteristics of almond (*Prunus dulcis*) flavor. *Journal of Agricultural and Food Chemistry*, **67** (10), 2743, **2019**.