Original Research

Production and Characterization of *Chlorella pyrenoidosa* Biomass Cultivated in Domestic Wastewater

Mohamed El Amine Dahou^{1, 2*}, Siham Dehmani¹, Chaima Dehmani³, Djamel Zerrouki⁴

¹Department of Hydrocarbons and Renewable Energies, Ahmed Draia University, Adrar-Algeria
²Catalytic materials and industrial processes laboratory, Ahmed Draia University, Adrar-Algeria
³University of Castilla-La Mancha, Faculty of Chemical Sciences and Technologies. Chemical Engineering Department
Av. Camilo José Cela, 1, 13005 Ciudad Real, Spain

⁴Univ. Ouargla, Fac. des sciences appliquées, Lab. dynamique interaction et réactivités des systèmes, BP 511, Route de Ghardaïa, Ouargla 30000, Algeria

Received: 5 April 2024 Accepted: 30 June 2024

Abstract

The simultaneous use of microalgae for algal biomass generation and wastewater treatment is a feasible strategy. Microalgae have long been recognized for their capacity to decompose organic materials, remove nutrients, and absorb heavy metals. According to the present study's experimental results, the biomass of C.pyrenoidosa contains 49% carbon, 7.06% hydrogen, 7.8% nitrogen, 0.65% sulfur, and 35.49% oxygen. There are three primary stages to the combustion of *C. pyrenoidosa*: the first is the removal of moisture (4.87%), the second is the devolatilization of proteins, lipids, and carbohydrates (57.13%), and the third is the degradation of carbonaceous materials (38%). These results highlight the considerable potential of using *C. pyrenoidosa* biomass as a feedstock for biofuel production.

Keywords: Microalgae, C. pyrenoidosa, Biofuel production

Introduction

The development of clean and renewable energy sources such as biomass, solar, and wind has led to the gradual depletion of main sources of fossil fuel energy, such as natural gas, oil, and coal, in recent decades. As a result, biomass conversion into biofuels has become one of the most important aspects of renewable energy for producing bioethanol and biodiesel from cultivated plants [1]. Microalgal-based biofuels have come to the fore as a potentially viable substitute to replace fossil fuels to attain energy security and environmental sustainability [2]. These tiny aquatic plants called microalgae are naturally found in wastewater. These fast-growing organisms (doubling in as little as a week or two) have a taste for nutrients, making them ideal

*e-mail: amine dahou@yahoo.fr

Tel.: +213661196915

candidates for wastewater treatment. Properly designed and operated systems using microalgae can potentially remove these nutrients from wastewater in a relatively simple setup. Microalgae accomplish this feat in two ways: either by using the organic matter in wastewater as fuel for their growth, or by directly absorbing the nutrients into their cells. It is important to note that high pH levels, common during algae treatment, may cause some ammonia to escape from the solution [3]. Many previous studies have shown that microalgae in wastewater treatment systems are considered a biorefinery strategy [4] due to their uncomplicated cell structure, faster growth rate, and higher lipid content compared to conventional oilseed crops [2]. Microalgal-based wastewater treatment offers several economic and environmental benefits beyond nutrient removal. Operational costs can be reduced due to the streamlined process. Furthermore, the microalgal biomass, rich in assimilated nitrogen and phosphorus, can be valorized as a biofertilizer, creating a valuable product from the treatment process. Additionally, the treated effluent is oxygenated, improving its environmental impact when discharged into water bodies. Following wastewater treatment, the harvested algae can be further utilized for biofuel production or co-digested with sludge to enhance biogas generation at treatment plants. These downstream applications can generate revenue for the treatment facility, contribute to green energy production, and ultimately reduce the plant's carbon footprint [5]. The most expansive microalgae species used for wastewater treatment are Spiruline [6], Botryococcus [7], Chlorella [8], and Scenedesmus [9]. Interestingly, several algae species habitually store between 50 and 60% of their dry weight as fat. This percentage has increased due to adaptation to different environmental and nutritional stress conditions [10]. However, it is important to note that stress-induced lipid accumulation usually leads to decreased biomass productivity [11]. Developing the right procedure for the industrial production of biofuels requires an understanding of the chemical and physical characteristics of microalgae. In this context, according to Yu et al. [12], lipid-rich microalgae may provide third-generation biofuels and chemicals in the future. In general, microalgae typically produce various types of lipids, such as wax esters, hydrocarbons, sterols, neutral and polar lipids, and prenyl derivatives including quinines, tocopherols, terpenes, and carotenoids, and pyrrole derivatives like chlorophylls [13]. C. pyrenoidosa is one of the microalgae strains that shows the most promise for treating wastewater and producing biofuel and platform chemicals [14]. Therefore, the main objective of this study is to evaluate the biomass of C. pyrenoidosa that can be used as feedstock for biofuels in terms of its chemical, microbiological, and biochemical properties.

Materials and Methods

Microalgae Strain preparation and Cultivation conditions

The Chlorella pyrenoidosa microalgae strain is used in this study, and the culture expansion was first processed in the laboratory. Chlorella pyrenoidosa was cultured in 500 ml of autoclaved agar media (BG11) in 1000 ml Erlenmeyer flasks and boosted in three 1000 ml conical flasks during the sterile inoculation process. The composition of nutrient per liter BG 11 medium was as follows: 0.001g of $C_{10}H_{16}N_2O_8$, 0.006 g of $C_6H_8O_7$, 0.02 g of Na₂CO₃, 0.036 g of CaCl₂H₂O, 0.075 g of MgSO₄7H₂O₅, 0.04 g of K₂HPO₄, 1.5 g of NaNO₃, and 1 ml of a solution containing trace elements with the following composition (g/L): 0.0494 of Co(NO₃)₂6H₂O, 0.079 of CuSO₄5H₂O, 0.39 of NaMoO₄2H₂O, 0.222 of ZnSO₄7H₂O₅, 1.81 of MnCl₂4H₂O and 2.86 of H₂BO₅. Every culture was placed in a closed culture that had red and blue LED lights installed. Uninterrupted air bubbling was used to mix the cultures, and the temperature was kept constant at 25°C. The suspension was then added to wastewater in an open raceway pond that had been detailed in previous research [15].

After growing in wastewater, the biomass of *C. pyrenoidosa* was collected using a centrifuge for 5 minutes at 10,000 rpm. After collection, the biomass was twice cleaned with distilled water and then left to dry overnight in an oven at a temperature of 80°C.

Ultimate Analysis

The ultimate composition of *C. pyrenoidosa* was carried out using a CHNS/O Elemental Analyzer (PerkinElmer®: 2400 Series II). A tin capsule containing about 1 mg of the sample was weighed before being put inside the automated sampler. For analysis, the temperature was set at 1000°C. As vector gases, helium, nitrogen, and oxygen were employed. Using the Dulong formula [16], the higher heating value (HHV) of the biomass of *C. pyrenoidosa* was determined from the final analytical results as follows:

$$0.3383 \times C + 1.443 \times H - 0.1804 \times O + 0.0942 \times S$$

Concentration of Mineral and Heavy Metals in Algal Biomass

One gram of dried Chlorella biomass was analyzed to determine the mineral and heavy metal content using the method of inductively coupled plasma atomic emission spectrometry (ICP-AES) using the procedure described by Khani et al. [17]. The sample preparation involved microwave digestion. Specifically, the biomass was digested in a Teflon capsule with 10 ml of 65% nitric acid and 0.5 ml of hydrogen peroxide for 40 minutes. After digestion, the resulting solution was filtered through a 45-micrometer filter. The filtrate was then

diluted to a final volume of 40 ml with doubly distilled water before analysis.

Determining Lipid Content

A modified method of Bligh and Dyer's method was used to extract total lipids from algal biomass [18]. A 15 ml test tube containing 50 mg of dried algal biomass was filled with 2.0 ml of chloroform, 4.0 ml of methanol, and 1.6 ml of water. The result solution was mixed for approximately 30 seconds. Subsequently, 2.0 ml of water and 2.0 ml of chloroform were added to the test tube, and then mixed for 30 seconds. Next, the test tubes were then centrifuged for 10 minutes at 5000 rpm. After that, using a pipette, remove the top layer and transfer the extracted lipids contained in the bottom chloroform phase into a 30 ml culture tube. The same process was used twice more to extract the solid material that remained at the bottom of the extraction tube. The chloroform phases were combined and evaporated in a rotating evaporator until the production of dried lipids. The lipid content was calculated after measuring the total lipids using gravity.

Scanning Electron Microscopy of Algal Biomass

For their morphological studies, the dried biomass of *C. pyrenoidosa* and the calcined biomass at 500°C and 1200°C were screened using ProX SEM (Scanning Electron Microscopy Phenom). Utilizing energy dispersive X-ray (EDX) spectroscopy, the composition of the calcined biomass was examined. To reduce the surface's electron charging impact, the samples were dried and placed on PELCO TabsTM Carbon Conductive Tabs, Double Coated.

FTIR Analysis

Attenuated total reflectance (ATR) spectra were obtained using an Agilent Cary 630 FTIR Spectrometer, which was equipped with a diamond crystal ATR reflectance cell and a DTGS detector. The spectra were scanned across the range of 4000 to 400 cm⁻¹ with a resolution of 4 cm⁻¹. Approximately 4-6 mg of dried algal biomass was placed on the crystal surface and pressed onto the crystal head. Prior to each sample scan, background correction scans of ambient air were conducted. The spectroscopic software Spectrum (Micro lab) was used to record the scans, which were further corrected for ambient air. The diamond ATR was cleaned with ethanol between samples.

Thermogravimetric Analysis

This parameter was performed using the TA Instruments DSC SDT Q600 Thermogravimetric Analyzer (TGA). To reduce the impacts of mass and heat transmission during the process, particles smaller than 20 μ m were used after the algal biomass was

sifted. 12.0550 mg of dried *C. pyrenoidosa* biomass was dispersed in an alumina crucible. The pyrolysis process was carried out at ambient temperature and gradually increased to 900°C at a rate of 10°C/min. A flow of high-purity nitrogen (99.99%) at a rate of 100 ml/min was used as an inert-gas to displace air during the process, avoiding undesired oxidation in the biomass. During pyrolysis, weight loss was recorded according to temperature. The rate of weight loss in biomass (dx/dt) was recorded as a derived thermogravimetric curve (DTG).

Results and Discussions

Ultimate Analysis

Table 1 shows the results of the ultimate analysis and the higher heating value of C.pyrenoidosa. According to these results, the proportions of carbon, hydrogen, nitrogen, sulfur, and oxygen in C.pyrenoidosa in this study were 49, 7.06, 7.8, 0.65, and 35.49%, respectively. These compositions are similar to the previously reported data by Chen et al. [19]. As indicated in Table 1, Sagarssum sp and Ulva-prolifera have higher levels of oxygen and lower levels of carbon content in comparison to our microalgae. The high carbon content of the microalgae biomass makes it highly thermochemically promising for the manufacture of biofuels. In contrast, for biofuels with high energy density, a high level of oxygen is not a preferred characteristic. A low nitrogen and sulfur content in the microalgae biomass is highly desirable for the production of environmentally friendly biofuels. The ratios of H/C and O/C of C. vulgaris were 0.144 and 0.724, respectively. The nitrogen content in C.pyrenoidosa was relatively high (7.8%), as compared to other microalgae strains such as Sagarssum sp, U.prolifera, and Chlorella vulgaris at 0.35, 3.00, and 6.01% [20-22], respectively, though not as high as observed concentrations in C.pyrenoidosa at 8.03% [23]. The biomass's HHV was measured at 20.44 MJ kg⁻¹, which was higher than the results of previous studies that were released. This can be explained by the higher levels of carbon and hydrogen present in C.pyrenoidosa. According to Illman et al. [10], a gain in higher heating value in microalgae is not related to changes in other cellular constituents, such as proteins and carbohydrates, but rather to an increase in lipid content.

Concentration of Mineral and Heavy Metals in Algal Biomass

Mineral analysis of microalgae biomass also provides valuable information for microalgae culture in terms of nutrient requirements. According to Valverde (2014) [24], the zinc, aluminum, and sodium concentrations are lower than those found in our study. Similarly, *Nannochloropsis* contain higher amounts of manganese and iron than *C. pyrenoidosa* [24]. The results show that

	Literature			In this study	
Composition (%)	Ulva-prolifera [20]	Sagarssum sp [21]	Chlorella. sp [22]	C. pyrenoidosa [23]	C. pyrenoidosa
С	46.20	21.11	53.91	47.09	49.00
Н	07.40	04.26	07.71	07.45	07. 06
N	3.00	00.35	06.01	08.03	07. 8
S	00.2	02.90	00.43	01.31	00.65
О	43.20	56.73	31.95	21. 62	35. 49
HHV (MJ kg ⁻¹)	16.54	-	23.52	-	20. 44

Table. 1. Ultimate analysis of microalgae.

the amount of mercury in *C. pyrenoidosa* (0.154 ppm) was negligible as compared to *Scenedesmus almeriensis* (80 ppm). The results summarized in Table 2 show that the concentration (ppm) of Chrome, Plomb, Cadmium, Arsenic, and Nickel in the biomass were 1.67, 23.59, 1.55, 1.84, and 5.1, respectively.

Scanning Electron Microscopy of Algal Biomass

The characteristics of algal biomass depend on the harvesting technique, environmental conditions, propagation medium, and cultivation period. SEM image showed a spherical morphology for the sample.

Table. 2. Concentration of minerals and heavy metals in microalgae.

Elements (ppm)	In this study	Literature			
	CD	CV	SC	NG	
	CP	[22]			
Na	6363. 89	5277	4402	41620	
Ca	2989. 86	10397	7297	7493	
Fe	1096. 4	711. 6	2768. 6	2414. 9	
Zn	2272. 61	177. 8	83. 9	77. 9	
Mn	159. 93	121. 8	469. 5	339. 6	
Cu	33. 52	144. 2	-	-	
Al	651.42	107. 3	106. 1	433. 1	
Si	1565	14817	11239	38394	
Hg	0. 154	-	80. 8	-	
Cr	1. 67	-	-	-	
Pb	23. 59	-	-	-	
Cd	1. 55	-	-	-	
As	1. 84	-	-	-	
Ni	5. 1	-	-	-	

(CV) Clorella vulgaris, (SC) Scenedesmus almeriensis, (NG) Nannochloropsis gaditana

In a study conducted by Moreira et al. [25], it was found that Chlorella pyrenoidosa displayed a consistent spherical morphology, with particle sizes ranging from 14.13 μ m to 123.4 μ m and a median size of 38.84 μ m. Ponnuswamy et al. [26] reported that *C. vulgaris* was unicellular microalgae green in color and spherical in shape.

The form of shrinkage of the particles shown in Fig. 1 resulted from dehydration of C. pyrenoidosa during the drying process (calcination at 500°C). From Fig. 1, the EDX spectrograms of C. pyrenoidosa biomass calcined at 500°C give an approximate composition in (weight%): 2.3 of sulfur, 2.9 of potassium, 3 of sodium, 3.5 of calcium, 4.2 of magnesium, 4.3 of phosphorus, 4.5 of chlorine, 6.3 of silicon, 21 of oxygen, and 48 of carbon. Scanning electron microscopy of biomass calcined at 1200°C shows a representative SEM image of algal ash. The ash residue contains flakes as grains and some particles with irregular shapes (Fig. 1), the chemical composition is shown in the EDX spectrograms (Fig. 1), the inorganic elements present in the ashes were (Si, Mg, Ca, O, P, Cl, Na, N, S, P); these elements are present in the form of metal oxides such as SiO₂, CaO, MgO, NaO₂, P₂O₅, SO₃.

Lipid Content

The lipid profile can provide information for research on biofuels, such as the selection of microalgae strains and the enhancement of conditions for growth and microalgae extraction. According to several authors, a variety of factors, including nutrient conditions like the concentrations of C and N in the medium, the growth period, the physiology of the microalgae, and environmental conditions like temperature and salinity, can have a significant impact on lipid content. Additionally, the extraction yield can vary depending on the solvents and method used [27]. Due to their high rapid growth and lipid productivity, microalgae such as *Nannochloropsis* sp, *Scenedesmus* sp, and *Chlorella* sp are considered a promising source for the production of biofuel [28].

Therefore, many studies have been carried out to enhance the microalgae's lipid productivity

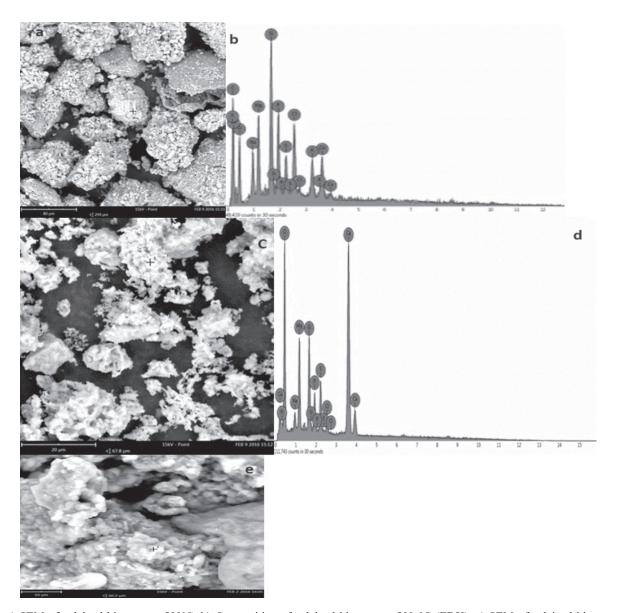


Fig. 1. a) SEM of calcined biomass at 500°C. b) Composition of calcined biomass at 500 °C (EDX). c) SEM of calcined biomass at 1200°C. d) Composition of calcined biomass at 1200°C (EDX). e) SEM image of *C. pyrendoisa*.

and production efficiency [29]. As shown in Table 3, the lipid content in *C.pyrenoidosa* was relatively high (23.2%), as compared to other microalgae strains such as *Chlamydomonas reinhardtii*, *Chlorella* sp, *Dunaliella bioculata*, and *Scenedesmus quadricauda* at 6, 16.5, 8 and 1.9%, respectively, though not as high as the observed content in *Amphora coffeaeformis*, *Dunaliella salina*, and *Pavlova salina*.

Infrared Spectrum

The FTIR spectrum of raw *Chlorella pyrenoidosa* and their residue is shown in (Fig. 2) with bands assigned according to literature [36]. As illustrated in Fig. 2, a total of eleven bands have been detected over the entire range number (4000-400 cm⁻¹), each peak having a functional group. These bands primarily represent

Table. 3. Lipid content of microalgae species.

Microalgae species	Lipid content by weight (%)	References
Amphora coffeaeformis	30	[30]
Chlamydomonas reinhardtii	6	[31]
Chlorella emersonii	29	[32]
Chlorella pyrenoidosa	23.2	In this study
Chlorella vulgaris	14 - 22	[33]
Chlorella sp	16.5	[34]
Dunaliella bioculata	8	[35]
Dunaliella salina	6	[35]
Pavlova salina	12-30	[35]
Scenedesmus quadricauda	1.9	[33]

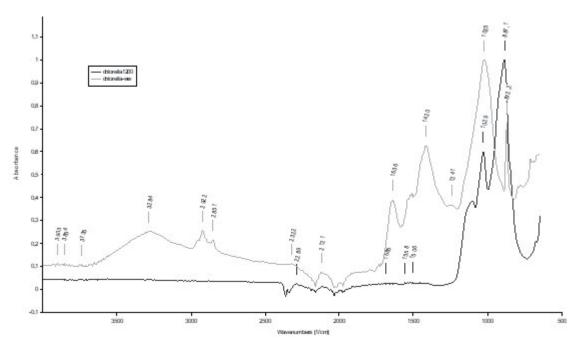


Fig. 2. FTIR spectra of dry C. pyrenoidosa biomass and calcined at 1200°C.

the cellular components such as carbohydrates, proteins, and lipids; a peak at 3277 cm⁻¹ indicates that a hydroxyl group's OH stretching and NH stretching in proteins. The band located at 2921 cm⁻¹ is associated with asymmetric and symmetrical elongations CH2 groups. The band at 2857 cm⁻¹ is assigned to the elongation (CH₂), (CH₂) of methyl and methylene groups [37]. The band between 2108 cm⁻¹ and 2334 cm⁻¹ could be assigned to CO₂ vibration mode, the band at 1792 cm⁻¹ comes from the symmetrical elongation of the C = O groups of the lipid and fatty acid esters. The symmetrical elongation of the C = O groups of the protein amides I induces a band around 1639 cm⁻¹ [36]. The band at 1529 cm⁻¹ is attributed to the symmetrical elongation (CH) of protein amides II and to the deformation of the groups (NH). Elongation of the COO, CH, and CH, groups of the protein DNA forms a band at 1416 cm⁻¹. The band located between 1020 and 957 cm⁻¹ assigned mainly to the symmetrical elongation (Si-O) of siloxanes, to the elongation (Si-OH) of silanols, to elongation (CO), and to elongation (P = O) RNA and DNA. The band between 866 and 839 cm⁻¹ is attributed to the asymmetric deformation of the silanol group (Si-OH) and the cell wall (polysaccharides). The infrared spectra of the biomass residue after calcination at 1200°C give three peaks. After calcination, the compounds present are mostly inorganic. The band at 1029 cm⁻¹ comes from the asymmetric elongation of Si-O-Si. The stretching associated with the peak at 1112 cm-1 indicates the presence of sulfates because they have a characteristic peak in this region. The presence of calcium carbonates (CaCO₃) is characterized by a peak between 1495 and 1410 cm⁻¹, and a mean peak between 885 and 870 cm⁻¹. This was mainly in accordance with EDX analysis.

Thermogravimetric Analysis

The results of biomass weight loss (TGA) and its corresponding rate (DTG) are illustrated in Fig. 3. According to the TGA curves for C. pyrenoidosa biomass sample, the results indicated that there were three distinct pyrolysis stages. The initial stage of pyrolysis took place at an ambient temperature of 144.95°C. This weight loss mainly results from the process of dehydration, which involves the removal of both intracellular and externally-bound water [38]. The type and storage of biomass can have a significant impact on the moisture content of the biomass. The choice of biomass conversion process is significantly influenced by the moisture content. High-moisturecontent biofuels are more suitable for biochemical techniques, whereas low-moisture biofuels are better suited for thermal conversion processes [39]. It is proposed that in a biorefinery design, the residual heat from the combustion of the pyrolysis gas can be used to dry the incoming biomass in order to decrease its moisture content if needed. The moisture content in C. pyrenoidosa in this study is 4.87%. Similarly, Ma (2020) [20] and Arif (2021) [23] have reported that Ulva prolifera and Chlorella sp have moisture contents of 11.00% and 7.29%, respectively. The main stage in this process is the second stage, characterized by the decomposition and depolymerization of the organic substances of microalgae, including proteins, carbohydrates, and lipids. This study indicated that the second stage occurred from 145°C to 767.8°C. Approximately 57.13% weight losses were observed for C.pyrenoidosa. Similar results had been reported for some other microalgae species, such as 44.85% for Sargassum natans according to Wang et al. [40], 55.37%

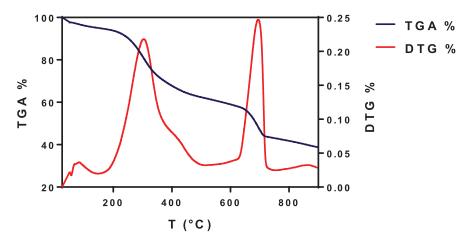


Fig. 3. TGA/ DTG analysis as a function of temperature

for C. vulgaris reported by Chen et al. [41], 55.6% for Chlorococcum humicola as mentioned by Kirtania et al. [42], and 68.79% for Saccharina japonica as found in the study by Kim et al. [43]. The generation of gases and liquid products during pyrolysis requires a high volatile content. The last stage (stage III) of pyrolysis was observed at 768°C. During this stage, a very small amount of weight loss was observed. This is mainly the result of the decomposition of the carbonaceous substances retained in the solid residues [44]. After the pyrolysis process, the final residue for C.pyrenoidosa accounted for 38%. Solid residues are mainly composed of fixed carbon and ash [45]. Chen et al. [41], reported that the total residue of C. vulgaris was 44%.

Conclusions

One of the most hopeful replacements for biofuel feedstocks is lipid and biomass derived from microalgae. According to the biomass characterization of *C. pyrenoidosa*, it was contaminated with two types of bacteria, namely Listeria grayi and Cellulomonas. sp. The final results of the ultimate analysis in this study indicated that microalgal biomass contains a high percentage of carbon (49%), and low nitrogen and sulfur, making it highly thermochemically promising and desirable for the production of environmentally friendly biofuels.

Acknowledgments

The authors thank the General Directorate of Scientific and Technological Research (DGRSDT) for the financial support of this research.

Conflict of Interest

The authors declare no conflict of interest.

References

- OSMAN A.I., MEHTA N., ELGARAHY A.M., Al-HINAI A., AL-MUHTASEB A.A.H., ROONEY D.W. Conversion of biomass to biofuels and life cycle assessment: a review. Environmental Chemistry Letters. 19, 4075, 2021.
- DANESHVAR E., WICKER R.J., SHOW P.L., BHATNAGAR A. Biologically-Mediated Carbon Capture and Utilization by Microalgae towards Sustainable CO₂ and biofixation and biomass valorization—A review. Chemical Engineering Journal, 427, 130884, 2022.
- WICKER R.J., KUMAR G., KHAN E., BHATNAGAR A. Emergent green technologies for cost-effective valorization of microalgal biomass to renewable fuel products under a biorefinery scheme. Chemical Engineering Journal, 415, 128932, 2021.
- BHATIA S.K., MEHARIYA S., BHATIA R.K., KUMAR M., PUGAZHENDHI A., AWASTHI M.K., ATABANI A.E., KUMAR G., KIM W., SEO S-O., YANG Y.H. Wastewater based microalgal biorefinery for bioenergy production: Progress and challenges. Science of the Total Environment, 751, 141599, 2021.
- ABDELFATTAH A., ALI S.S., RAMADAN H., EL-ASWAR E.I., ELTAWAB R., HO S.H., SUN J. Microalgae-Based Wastewater Treatment: Mechanisms, Challenges, Recent Advances, and Future Prospects. Environmental Science and Ecotechnology, 13, 100205, 2023
- GE S., BRINDHADEVI K., XIA C., KHALIFA A.S., ELFASAKHANY A., UNPAPROM Y., VAN DOAN H. Enhancement of the combustion, performance and emission characteristics of spirulina microalgae biodiesel blends using nanoparticles. Fuel, 308, 121822, 2022.
- DE LIMA N.A.M., ECARD L.G., RODRIGUES E., VEIGA L., SAMPAIO GUEDES C.E., ANDRADE S., CUNHA LIMA S.T. Use of Microalgae for Biofuel Production in the Northeast Region of Brazil, with Emphasis on Genus Botryococcus: A Review. Industrial Biotechnology, 18 (2), 77, 2022.
- 8. CORONADO-REYES J.A., SALAZAR-TORRES J.A., JUÁREZ-CAMPOS B., GONZALEZ-HERNANDEZ J.C. Chlorella vulgaris, a microalgae important to be used in Biotechnology: a review. Food Science and Technology, 42, e37320, 2020.
- MSANNE J., POLLE J., STARKENBURG S. An assessment of heterotrophy and mixotrophy

- in Scenedesmus and its utilization in wastewater treatment. Algal research, **48**, 101911, **2020**.
- ILLMAN A.M., SCRAGG A.H., SHALES S.W. Increase in Chlorella Strains Calorific Values When Grown in Low Nitrogen Medium. Enzyme and Microbial Technology, 27 (8), 631, 2000.
- SONG X., LIU B.F., KONG F., REN N.Q., REN H.Y. Overview on stress-induced strategies for enhanced microalgae lipid production: Application, mechanisms and challenges. Resources Conservation and Recycling, 183, 106355, 2022.
- YU D., XIE G., CHEN Q., YANG Y., DONG N. Biofuel potential of liquid products from protein-and lipidrich biomass hydrothermal liquefaction. Biomass and Bioenergy, 165, 106571, 2022.
- HUSSEIN KHORSHED B., AUSAMA AL-KATIB M. Screening of some algal oils to select the best algal biodiesel resource. Egyptian Journal of Aquatic Biology and Fisheries, 25 (3), 571, 2021.
- 14. RANA M.S., PRAJAPATI S.K. Stimulating Effects of Glycerol on the Growth, Phycoremediation and Biofuel Potential of Chlorella Pyrenoidosa Cultivated in Wastewater. Environmental Technology & Innovation, 24, 102082, 2021.
- DAHMANI S., ZERROUKI D., RAMANNA L., RAWAT I., BUX F. Cultivation of Chlorella Pyrenoidosa in Outdoor Open Raceway Pond Using Domestic Wastewater as Medium in Arid Desert Region. Bioresource Technology, 219, 749, 2016.
- 16. CHEN J., DING L., WANG P., ZHANG W., LI J., MOHAMED B.A., CHEN J., LENG S., LIU T., LENG L., ZHOU W. The estimation of the higher heating value of biochar by data-driven modeling. Journal of Renewable Materials, 10, 1555, 2022.
- KHANI M.H., KHAMSEH A.G. Statistical analysis, equilibrium and dynamic study on the biosorption of strontium ions on Chlorella vulgaris. Journal of Radioanalytical and Nuclear Chemistry, 332 (8), 3325, 2023
- BLIGH E.G., DYER W.J. A Rapid Method of Total Lipid Extraction and Purification. Canadian Journal of Biochemistry and Physiology, 37 (8), 911, 1959.
- CHEN C., LU Z., MA X., LONG J., PENG Y., HU L., LU Q. Oxy-Fuel Combustion Characteristics and Kinetics of Microalgae Chlorella Vulgaris by Thermogravimetric Analysis. Bioresource Technology, 144, 563, 2021.
- 20. MA C., GENG J., ZHANG D., NING X. Non-catalytic and catalytic pyrolysis of Ulva prolifera macroalgae for production of quality bio-oil. Journal of the Energy Institute, **93** (1), 303, **2020**.
- 21. LI Y., YU Z., CHEN L., TANG F., MA X. Fast catalytic co-pyrolysis characteristics and kinetics of chlorella vulgaris and municipal solid waste over hierarchical ZSM-5 zeolite. BioEnergy Research, 14, 226, 2021.
- 22. RUSTAMAJI H., PRAKOSO T., DEVIANTO H., WIDIATMOKO P., RIZKIANA J., GUAN G. Synthesis and characterization of hydrochar and bio-oil from hydrothermal carbonization of *Sargassum* sp. using choline chloride (ChCl) catalyst. International Journal of Renewable Energy Development, 11 (2), 403, 2022.
- 23. ARIF M., LI Y., EL-DALATONY M.M., ZHANG, C., LI X., SALAMA E.S. A complete characterization of microalgal biomass through FTIR/TGA/CHNS analysis: An approach for biofuel generation and nutrients removal. Renewable Energy, 163, 1973, 2021.

- 24. VALVERDE J.L. Kinetic Analysis and Thermal Characterization of the Microalgae Combustion Process by Thermal Analysis Coupled to Mass Spectrometry. Applied Energy, 114, 227, 2014.
- 25. MOREIRA V.R., LEBRON Y.A.R., FREIRE S.J., SANTOS L.V.S., PALLADINO F., JACOB R.S. Biosorption of Copper Ions from Aqueous Solution Using Chlorella Pyrenoidosa: Optimization, Equilibrium and Kinetics Studies. Microchemical Journal, 145, 119, 2019.
- 26. PONNUSWAMY I., MADHAVAN S., SHABUDEEN S. Isolation and Characterization of Green Microalgae for Carbon Sequestration, Waste Water Treatment and Bio-Fuel Production. International Journal of Bio-Science and Bio-Technology, 5 (2), 17, 2013.
- 27. NORDIN N., YUSOF N., SAMSUDIN S. Biomass Production of *Chlorella* Sp., *Scenedesmus* Sp., and Oscillatoria Sp. in Nitrified Landfill Leachate. Waste and Biomass Valorization, **8** (7), 2301, **2017**.
- 28. MOAZAMI N., ASHORI A., RANJBAR R., TANGESTANI M., EGHTESADI R., NEJAD A.S. Large-Scale Biodiesel Production Using Microalgae Biomass of Nannochloropsis. Biomass and Bioenergy, 39, 449, 2012.
- 29. GOH B.H.H., ONG H.C., CHEAH M.Y., CHEN W.H., YU K.L., MAHLIA T.M.I. Sustainability of direct biodiesel synthesis from microalgae biomass: A critical review. Renewable and Sustainable Energy Reviews, 107, 59, 2019.
- SING M.F. (2010). Strain selection and outdoor cultivation of halophilic microalgae with potential for large-scale biodiesel production (Doctoral dissertation, Murdoch University).
- 31. SACHDEVA N., GUPTA R.P., MATHUR A.S., TULI D.K. Enhanced lipid production in thermo-tolerant mutants of Chlorella pyrenoidosa NCIM 2738. Bioresource technology, 221, 576, 2016.
- MORALES M., AFLALO C., BERNARD O. Microalgal lipids: A review of lipids potential and quantification for 95 phytoplankton species. Biomass and Bioenergy, 150, 106108, 2021.
- WOOD D.A. Microalgae to biodiesel-Review of recent progress. Bioresource Technology Reports, 14, 100665, 2021
- 34. BEHERA B., UNPAPROM Y., RAMARAJ R., MANIAM G.P., GOVINDAN N., PARAMASIVAN B. Integrated biomolecular and bioprocess engineering strategies for enhancing the lipid yield from microalgae. Renewable and Sustainable Energy Reviews, 148, 111270, 2021.
- 35. SAJJADI B., CHEN W.Y., RAMAN A.A.A., IBRAHIM S. Microalgae lipid and biomass for biofuel production: A comprehensive review on lipid enhancement strategies and their effects on fatty acid composition. Renewable and Sustainable Energy Reviews, 97, 200, 2018.
- 36. MAHAPATRA D.M., RAMACHANDRA T.V. Algal biofuel: bountiful lipid from Chlorococcum sp. proliferating in municipal wastewater. Current science, 105 (1), 47, 2013.
- 37. BECIDAN M., SKREIBERG Ø., HUSTAD J.E. NO x and N₂O precursors (NH₃ and HCN) in pyrolysis of biomass residues. Energy & Fuels, **21** (2), 1173, **2007**.
- 38. PENG W., WU Q., TU P. Pyrolytic characteristics of heterotrophic Chlorella protothecoides for renewable biofuel production. Journal of Applied Phycology, 13, 5, 2001.
- 39. KASSIM M.A., KIRTANIA K., DE LA CRUZ D., CURA N., SRIVATSA S.C., BHATTACHARYA S. Thermogravimetric analysis and kinetic characterization of lipid-extracted Tetraselmis suecica and Chlorella sp. Algal Research, 6, 39, 2014.

- WANG S., WANG Q., JIANG X., HAN X., JI H. Compositional Analysis of Bio-Oil Derived from Pyrolysis of Seaweed. Energy Conversion and Management, 68, 273, 2013
- 41. CHEN C., MA X., LIU K. Thermogravimetric Analysis of Microalgae Combustion under Different Oxygen Supply Concentrations. Applied Energy, 88 (9), 3189, 2011.
- 42. KIRTANIA K., BHATTACHARYA S. Application of the Distributed Activation Energy Model to the Kinetic Study of Pyrolysis of the Fresh Water Algae Chlorococcum Humicola. Bioresource Technology, 107, 476, 2012.
- KIM S.S., LY H.V., CHOI G.H., KIM J., WOO H.C. Pyrolysis Characteristics and Kinetics of the Alga Saccharina Japonica. Bioresource Technology, 123, 445, 2012.
- 44. LIU Y.Q., LIM L.R., WANG J., YAN R., MAHAKHANT A. Investigation on Pyrolysis of Microalgae Botryococcus braunii and Hapalosiphon sp. Industrial & engineering chemistry research, **51** (31), 10320, **2012**.
- 45. AJAY K., LIJUN W., YURIS A.D., DAVID D.J., MILFORD A.H. Thermogravimetric characterization of corn stover as gasification and pyrolysis feedstock. Biomass and bioenergy, **32** (5), 460, **2008**.